



Carbon Nano Based Materials and Their Composites for Gas Sensing Applications: Review

Mohamed Morsy^{1,2*}, Amir Elzwawy³, Marwa Oraby⁴



CrossMark

1 Building Physics and Environment Institute, Housing & Building National Research Center (HBRC), Dokki, Giza, 12311, Egypt

2 Nanotechnology Research Centre (NTRC), The British University in Egypt (BUE), Suez Desert Road, El-Sherouk City, Cairo, 11837, Egypt.

3 Ceramics Department, Inorganic Chemistry Industries and Mineral Resources Research Division, National Research Centre, 33 El Bohouth St., Dokki, Cairo, 12622, Egypt

4Polymers Department, Chemistry Industries Research Division, National Research Centre, 33 El Bohouth St., Dokki, Cairo, 12622, Egypt

Abstract

The consequences of carbon nano materials incorporation for gas sensing applications received noteworthy consideration in the recent preceding years. Owing to their desirable physical and chemical specification, the carbon nanomaterials and combinations with other materials are well suited for the gas sensing applications as it satisfies the condition of elevated surface area and reduced bandgap. Herein, we start this review by reviewing the importance and preparation methods of carbon nanomaterials. Varied carbon based nanomaterials as carbon nanooxions, carbon nanohorns, nanodiamonds and carbon quantum dots are explored. Graphene and its derivatives are normally combined with CNTs, thus. We introduce after that the graphene synthesis, specifications, and graphene/metal oxides, noble metals, and polymers nanocomposites for gas sensing. This review summarized the keypoints for the gas sensing area that relied on carbon nanomaterials. Furthermore different types of sensors toward different gas species have been reported and discussed.

Keywords: Graphene; CNTs; Gas sensors; Nanomaterials; Carbon nanohorns

Outline

- | | |
|--|--|
| 1. Introduction | 6.3.1.1. Mechanical exfoliation |
| 2. Carbon nanohorns (CNHs) | 6.3.1.2. Chemical exfoliation |
| 3. Carbon nano-onions (CNOs) | 6.3.1.3. Pyrolysis of graphene |
| 4. Nano diamond (ND) | 6.3.1.4. Epitaxial growth of graphene |
| 5. Carbon Quantum Dots (CQDs): | 6.3.1.5. Chemical vapor deposition (CVD) |
| 6. Carbon nanotubes (CNTs) | 6.3.2. Graphene/ polymers for gas sensing: |
| 6.1. CNTs synthesizing techniques | 6.3.3. Graphene / metal oxide nanocomposite for gas sensing: |
| 6.2. CNTs for gas sensing | 6.3.4. Graphene / metals nanocomposite for gas sensing |
| 6.2.1. Carbon nanotubes/metal oxides for gas sensing | 6.3.5. Three-dimensional graphene and graphene foam. |
| 6.2.2. Carbon nanotubes/metals for gas sensing | Conclusion |
| 6.2.3. Carbon nanotubes/ organic materials for gas sensing | 1. Introduction |
| 6.3. Graphene | |
| 6.3.1. Synthesis of graphene | |

*Corresponding author e-mail: Mohamed.Morsy@bue.edu.eg, 83morsy@gmail.com

Receive Date: 06 October 2021, Revise Date: 01 March 2022, Accept Date: 01 November 2021

DOI: [10.21608/ejchem.2021.99842.4641](https://doi.org/10.21608/ejchem.2021.99842.4641)

©2022 National Information and Documentation Center (NIDOC)

Carbon is one of the most abundant elements on the planet, as it grasps the ability to produce an enormous number of bonds that can be formed with different materials or with itself. Besides, carbon allotropes exist as the carbon can hybridize in sp , sp^2 and sp^3 configurations.

From another point of view, carbon is exclusive among the elements due to its ability to adopt extended two-dimensional sheet structures in elemental form. Since the in-sheet bonding is tremendously strong, these sheets are stable both as isolated objects (graphene), and when turned into cylindrical geometries (nanotubes) or quasispherical geometries (fullerenes) wherein, e.g., pentagonal rings provide the needed Gaussian curvature. The carbon nanocone, is an intermediate state between graphene and fullerene wherein a single pentagonal ring or assembly of nearby pentagonal rings defines a conical apex, which is then extended by a pure-hexagon graphenic network into a larger conical structure [1].

In this review, we shed light on the carbon nanomaterials and their composites with different materials (i.e., metal oxides, polymer, metals, etc.) and their applications as gas sensors. These carbon nanomaterials comprise carbon nanohorns, carbon nano-onions (CNOs), nano diamond, carbon quantum dots (CQDs), carbon nanotubes (CNTs), and Graphene as represented in fig. 1. Remarkable attention has been devoted to both CNTs and graphene as they are extensively considered. In what follows we point out the most characteristic sorts of carbon nanomaterials.

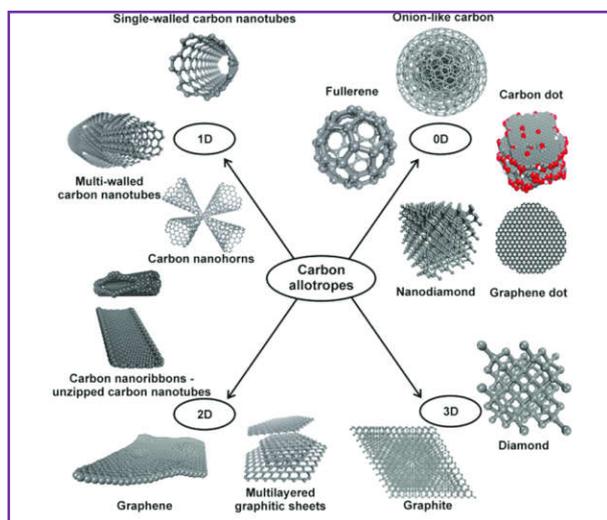


Figure 1: The illustration of allotropes of carbon nanomaterials, from [2]CC BY 4.0

2. Carbon nanohorns (CNHs):

Carbon nanohorns (CNHs) is belonging to the carbon nanomaterials family that have horn shaped tips and are closely similar to single wall carbon nanotubes (SWCNTs) as exposed in fig. 2. The essential characteristics of CNHs are their affinity to group together to form spherical clusters with overall dimensions of 2–5 nm in diameter and a length around 40–50 nm [1]. The three different forms of CNHs are dahlia-like flowers, bud-like flowers, and seed-like flowers [3]. Despite their unique advantages that are represented as high surface area, elevated electrical and thermal conductivity, and ease of functionalization, they are synthesized by laser ablation of pure graphite without the use of catalyst at room temperature with high yield and production rate [4][5].

Due to their high surface area and a large number of cavities, CNHs are promising candidates in different applications [6] like drug delivery [7], magnetic resonance analysis [8], photodynamic therapy [9] biosensing [10] and gas sensors. Suehiro et al. utilized dielectrophoresis (DEF) technique to fabricate CNHs gas sensor. The DEP-fabricated CNHs sensor was evaluated toward nitrogen dioxide (NO_2) and ammonia (NH_3) gas utilizing impedance spectroscopy. They demonstrated that the CNHs could detect the presence of ppm-levels of NH_3 and NO_2 gases at room temperature [11]. Sano et al. reported a simple and cost-effective method for producing CNHs and studied their gas sensing properties. They confirmed that the CNHs gas sensor can detect NH_3 and O_3 at room temperature. Their results demonstrated that gas sensors based on CNHs exhibited higher sensitivity compared to the sensor based on SWCNTs at the same conditions. They correlated this enhancement to mono-layer gas adsorption and the interaction of adsorbed gas molecules which affects the charge transfer from gas molecules to the sensor surface [12]. The applicability of carbon nanohorns can be extended as well for humidity sensing with the oxidized nanohorns as an active sensing layer. Sensing performance was tested within a 10-90% humidity of nitrogen and air. The sensitivity in air outcomes the sensitivity in humid nitrogen with a factor of two. Carboxylic groups existence can clarify this as the dealings with water molecules (as electron donors) declines the number of holes and oxidized single-walled carbon nanohorns develops higher resistivity [13].

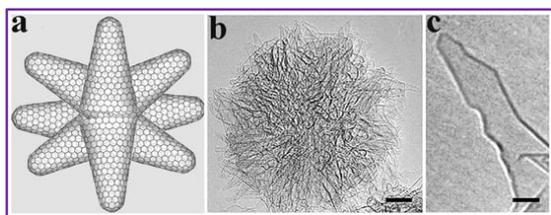


Figure 2:(a) Schematic demonstration of the carbon nanohorns, (b) The high-resolution transmission electron microscope (HRTEM) for the nanohorns, and (c) HRTEM for separate carbon nanohorn where the scale bar is set as 2 nm, from [14] CC BY 4.0

3. Carbon nano-onions (CNOs):

Carbon nano onions (CNOs) depicted in fig 3 are an allotrope of carbon nanomaterials belonging to the fullerene family, they are made of spherical, quasi-spherical, and polyhedral with concentric graphitic shells [15][16]. CNOs consist of multiple graphitic shell structures which can be defined by the series: $C_{60}@C_{240}@C_{540}@C_{960}@C_{1500}@C_{60n}$..., where n is the shell number [17]. Many synthesizing methods like thermal annealing of nanodiamonds (NDs) [18], arc discharge [19], flame assisted pyrolysis [20], chemical vapor deposition (CVD), and non-thermal plasma [21] have been explored to obtain CNOs. The outstanding properties of CNOs represented in high specific surface area, amazing electrical conductivity, and excellent tribological behavior could be due to their exclusive shell-shaped structure [16]. The above-mentioned properties of CNOs nominate it as a suitable material to be applied in many applications such as optical limiting, catalysis, energy storage, supercapacitors, lubricants, electrochemical sensors, and gas sensors [15]. To the best of our knowledge, limited studies have been focused on the gas sensing properties of CNOs. Dhonge et al investigated the gas sensing mechanism of CNOs toward volatile organic compounds (VOCs) at room temperature. They demonstrated that there was a linear relationship between sensitivity and gas concentration in the range of 34–148 ppm [22] as displayed in fig.4.

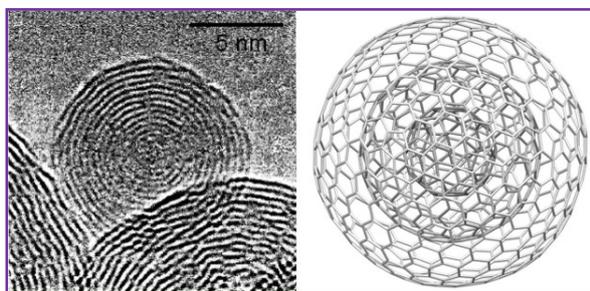


Figure 3: Carbon nanoonions, taken from [23] CC BY 4.0.

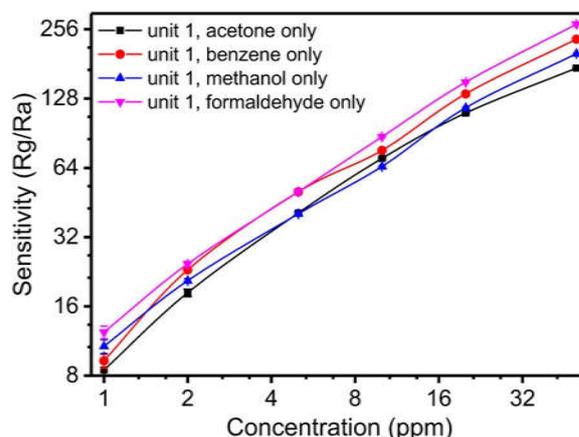


Figure 4: The sensitivity and gas concentration relationship for varied gases, obtained from [24]CC BY 4.0.

4. Nano diamond (ND):

Nano diamond (ND) is a zero dimension carbon Nano allotrope consisting primarily of short-range order tetrahedral SP³ bonded carbon atoms [25][26]. ND can be produced by three main industrial production technologies. The first technology is the mechanical grinding of high-quality diamond microcrystals produced under extreme conditions (High -temperature and high-pressure HTHP) from graphite. The second one is comprising the detonation synthesis from explosives. While the third one is CVD. The ND produced at extreme conditions is available with a particle size around 10–25 nm. The typical size of ND produced by the detonation method as estimated from XRD is 4–5nm [27]. Recently atmospheric pressure microplasma (AMP) has been considered as better choice as compared to the most commonly used detonation, HTHP and CVD [28]. NDs can be implemented in many applications such as magnetic resonance imaging, chromatography, electrochemical double-layer capacitors and batteries. Furthermore, lubrication, drug delivery and gas sensors [26][29]. This could be attributed to their exceptional chemical mechanical and optical properties. Referring to the gas sensing area of application, the synthesis of MWCNTs was executed employing nanocrystalline diamonds and the CVD procedure. In brief, the synthesized materials possess a rapid response for H₂ gas detection. Further selectivity and repeatability were affirmed for a sustained duration of 2 months. The elevated response/recovery attitude might be referred to the rise of defect locations because of ND grains existence which subsequently promotes the formation of multiple binding sites for the hydrogen molecules [30].

5. Carbon Quantum Dots (CQDs):

Carbon quantum dots (CQDs) are a novel member of zero-dimensional carbon-based nanomaterials having a particle size less than 10nm in diameter which is characterized by relatively strong fluorescence, biocompatibility, high thermal stability, inactive chemical structure and ease of functionalization [31]. CQDs maintain a significant sum of elevated specifications, to recite some, decent photoluminance, facile preparation methodologies, low- cost, reduced level of toxicity, as well as simple functionalization. Recently, CQDs deemed the application in the sensing area with a fine detection limit within nano-, pico- or even femtomolar amounts[32]. The incorporation of ZnO onto CQDs matrix to form a composite through the conventional hydrothermal route is conducted. This composite is applied for the sensing and monitoring of nitric oxide (NO) gas. The seizing of a recovery/ response times of 34, 36 s correspondingly is attained for a 100 ppm concentration detection limit. The NO₂ detection is further detected using the silica aerogels functionalized CQDs. In this work, the verified selectivity of the NO₂ gas amongst diverse gases as O₂, CO₂, and NH₃ is confirmed [33]. Aligning with this gas sensing for carbon dots, the composite of carbon dots reinforced with MgO nanoparticles was synthesized and exploited for the detection of H₂S gas using engineered Schottky apparatus. The I-V tendency for the sensor is assessed in air and targeted gas as well.

Inherently, the external voltage of -0.7 V for the 120 ppm gas concentration reports an elevated response of 11 times larger than the MgO. The noticeable diminish of the barrier height emerged during the H₂S gas exposure is responsible for the raised response of the aforementioned gas than other gases[34]

Ammonia gas sensor is employed using graphene quantum dots fabricated by a simple solution fabrication method at ambient conditions. Interestingly, a flexible modulation of the pH value from acidic to neutral results in a two contrary current responses for the gas[35].

6. Carbon nanotubes (CNTs)

Throughout the preceding three decades, the employment of CNTs in diverse applications is increased due to their eminent physical and chemical characteristics. Furthermore, CNTs have been in the eyes of researchers due to their exceptional thermal, electrical, chemical properties, stability, virtuous elastic modulus (1 ~TPa), high aspect ratio (50-500), strength ~100GPa), high stiffness and low density (~1.2 g/cm³ to ~1.8 g/cm³).

Starting from 2013 the researchers directed their interest for the designing of metal-organic frameworks reinforced CNTs for the energy appliances[36][37]. Besides, they are employed in the solar system nanofluids as CNTs are significantly characterized by elevating thermal and optoelectronic specifications of the nanofluid[38]. The evolving of medical applications for CNTs is provided as well thanks to the increased surface atoms ratio which might feasibly modulate the physicochemical specifications and promote higher chemical reactivity [39]. Commonly, there are two sorts of CNTs relied on their morphologies, either as single-wall carbon nanotube (SWCNTs) or multiwall carbon nanotube (MWCNTs). The SWCNTs are made up of a single graphene layer rolled in a cylindrical form (Fig:5(a)) while, for MWCNTs multiple layers of graphene (Fig:5(b)) are twisted into a cylindrical tube shape[40–42]. The CNTs (SWCNTs and MWCNTs) have been examined and tested to be utilized in various applications. Nowadays CNTs can be found approximately in all applications and industries, including medicine, pharmacy, agriculture, materials science, engineering, electronics, water treatment, solar cells, etc.

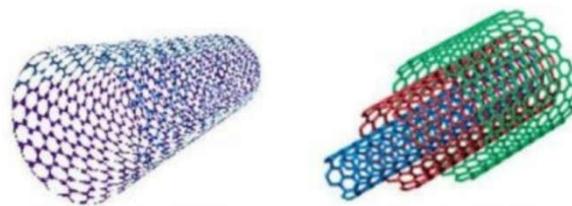


Figure 5: The visual illustration of (left) single wall carbon nanotubes (SWCNTs), and (right) multiwall carbon nanotubes (MWCNTs), acquired from [23]CC BY 4.0

6.1. CNTs synthesizing techniques:

Due to their outstanding properties, many synthesizing methods have been utilized for CNTs. All of these methods are categorized into three main techniques, stated as: arc discharge[43], laser ablation[44], and CVD[45] as represented in fig 6. The first utilized technique was arc discharge which consists of two carbon electrodes (anode and cathode) connected to low voltage high current DC power supply under inert media. The anode is filled with a mixture of powdered carbon precursors and catalysts.

The arc discharge is the first introduced technique for CNTs synthesizing. Simply described as the generation of plasma because of the electrical breakdown of the gas[46]. Generally, an arc is

introduced between a couple of graphitic rods separated by few nanometers. This process produces highly pure and defect-free CNTs, and it delivers a low cost and reduced time compared with other methods for CNTs synthesis[47].

However it suffers from many drawbacks represented in low yield which suppresses its practical applications[46, 48]

The laser ablation method for CNTs synthesizing comprises the evaporation of carbon from high pure carbon electrode using a laser beam at elevated temperatures. The laser ablation method is not extensively utilized as it consumes high energy and requires expensive equipment [43].

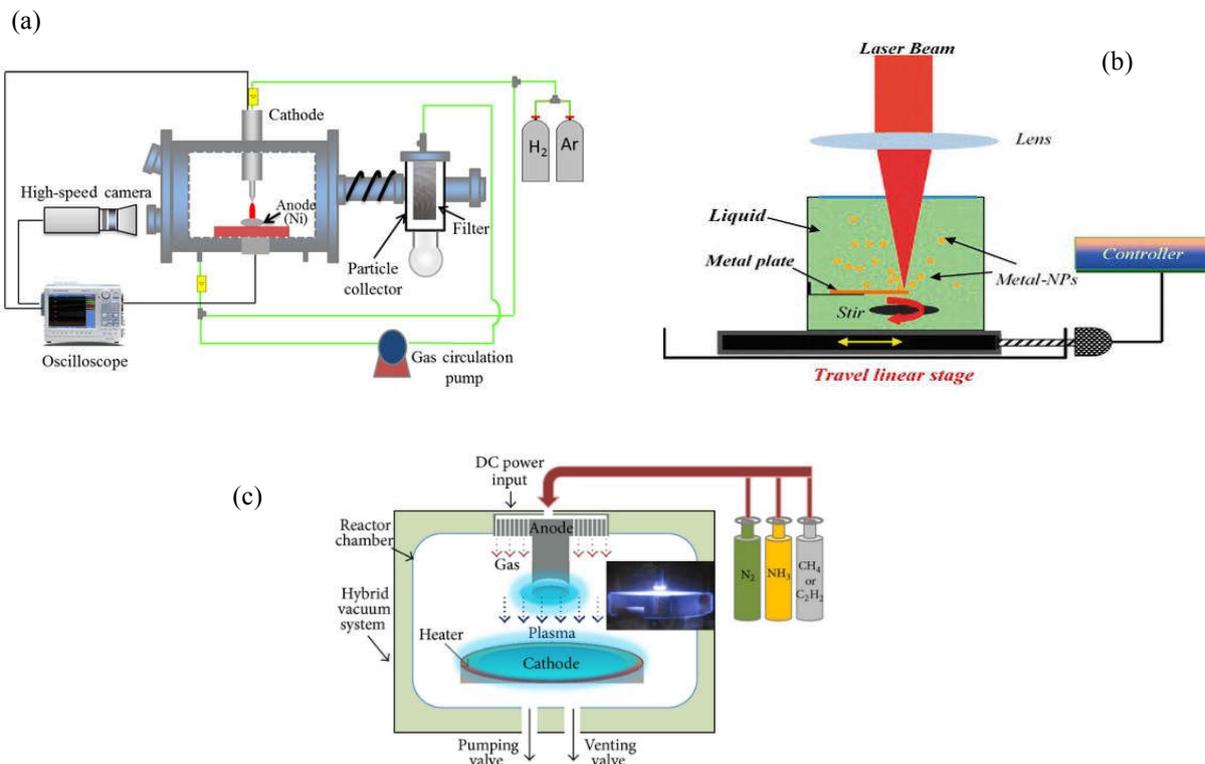


Figure 6: The most conventional CNTS synthesis techniques, (a) the arc discharge process, (b) laser ablation method, and (c) the chemical vapor deposition process. The attained figures are from open sources as [49] CC BY 4.0, [50] CC BY 3.0, and [51]CC BY 4.0, respectively.

CVD involves the decomposition of carbon species over a catalyst at relatively a high temperature to form CNTs. Among other synthesizing techniques (arc discharge and laser ablation), CVD is the most versatile technique for CNTs synthesizing. It is characterized by low production cost, high yield and the ability to produce different types of CNTs. Nowadays, CVD can be considered as the most trusted technique for mass production of CNTs[52].

6.2. CNTs for gas sensing:

The carbon nanotube is the most studied material for gas sensing applications. This is due to its high aspect ratio, chemical, thermal and mechanical stability, metallic and semi-conductive properties and functionalization capability that facilitate the adsorption of gas molecule on its surface. CNTs

suffer from a change in their conductivity as they interact with adsorbed gas molecules. Compared to conventional metal-oxide gas sensors, they have the advantage of detecting the presence of gases at room temperature. However the pristine CNTs cannot differentiate between different gases, as they suffer from poor selectivity [53]. Furthermore, the sensing mechanism of pristine CNTs is slightly complicated as they generally consist of a mixture of metallic and semiconducting tube, beside the different level of defects that resulted from purification processes. From this respect, modification/functionalization has been proposed to overcome poor sensitivity and selectivity [54]. Kinds of researches have been executed regarding the modification of CNTs with different materials. through this review, a summary of CNTs modified with inorganic and organic species will be exploited, especially for gas sensor devices with enhanced selectivity and sensitivity.

6.2.1. Carbon nanotubes/metal oxides for gas sensing

A variety of metal oxides semiconductors has been anchored to CNTs through different physical and chemical routes [55]. The main purpose of the decoration process is to promote the selectivity and sensitivity of CNTs for gas sensing applications. Both SWCNTs and MWCNTs have been studied extensively and some of the recent studies will be reviewed hereinafter. The SWCNTs are configured into gas sensors for a variety of poisonous gases like NH₃, NO, and NO₂. The SWNT-Fe₂O₃ composite film demonstrates a steady response and enhanced sensitivity for H₂S and shows enhanced sensitivity to NO₂ and at room temperature compared with pristine SWNT films. These flexible sensors with high deformability possibility can serve as wearable monitoring devices [56].

The combination of ZnO and SWCNTs is investigated for the detection of ethanol gas. The synthesis process is the spray pyrolysis of the nanostructured materials on a copper substrate. The optimum device performance is displayed at a 6% concentration of ZnO/SWCNT by weight. The chemisorption is the reason for the gas sensor response, in which the exchange of the charges between the metal oxide surface and the adsorbed gas species is attained [57].

The gas sensing for NO₂ is also developed using the same SWCNTs coated ZnO prepared by wet chemical process, where the response and recovery times are 70 and 100 s consecutively. Best conditions for sensing performance are acquired for 1000 ppm NO₂ at 150 °C [58].

The electrochemical synthesis method is also conducted for the gas sensing evaluation using ZnO/SWCNTs hybrids. Room temperature performance for varied gases of CO, CO₂, NO₂, H₂S, O₂, and NH₃ is executed. By finely adjusting the electrochemical factors, density, crystallinity, and subsequent particle size, a noticeable impact on the ambient conditions gas sensing attitude is monitored. In short, the functional ZnO/MWCNTs reveals almost 5% per ppm compared to 0.2 % for the non-functionalized MWCNTs for the H₂S gas.

A combination of SnO₂ and TiO₂ carbon nanotubes were prepared via a feasible sol-gel method for ethanol detection. The mixture demonstrates good quality as thermal stability and elevated sensitivity within a wide temperature span of room temperature to 250 °C [59]. The exploitation physical properties and gaseous monitoring in MWCNTs filled with vanadium oxide was

demonstrated. Methane gas detection response approached 16 seconds at room temperature, which was attributed to the density of states increase amongst Fermi energy level for the composite. Stress and highlights on the impact of ambient oxygen in CNTs-based sensors were addressed [60]. Cháfer et al explored the possibility of detecting both of NO₂ and NH₃. Using IrOx-MWCNTs nano composite. They demonstrated that IrOx-MWCNTs nano composite can detect NO₂ and NH₃ at different working temperatures with good reproducibility, higher sensitivity as low as 1 ppb, stability, and lower noise levels in comparison to pristine MWCNTs [61]. The MWCNTs doped ZnO is applied as a toluene gas sensor. Briefly, a variation of ZnO/MWCNTs is delivered which was synthesized by the reflux procedure. MWCNTs hinders agglomerations preparation for ZnO nanostructures. The ratio of 3:1 ZnO: MWCNTs reveals a 17% elevation of the sensor response at 150 °C compared with the pristine ZnO that doesn't introduce any response at the mentioned temperature [62]. The room temperature operated ammonia gas sensor was developed by T. Guo et al. They utilized a CNTs/Fe₃O₄ composite to detect a low concentration of ammonia at room temperature. They subjected CNTs/Fe₃O₄ sensor for ammonia concentrations of 20, 40, 60, and 80 ppm. The results demonstrated that the sensor responds selectively for ammonia with a short recovery time. Besides these advantages, the sensor has good linearity, good repeatability and long term stability [63] as shown in fig. 7.

The MWCNTs decorated ZnO nanostructures are prepared for the hydrogen gas sensing. To enhance the performance, Pt nanoparticles deposited by sputtering are employed on the composite surface. 78 s recovery time is approached, as well as decent repeatability and stability for 0.05% amount of the targeted gas at surrounding room temperature. Moreover, the MWCNTs/ZnO/Pt reaches 4% sensitivity which is almost a duplication of the MWCNTs/ZnO itself [64].

The nanostructure of Al₂O₃/CeO₂/MWCNTs was successfully prepared by the conventional chemical precipitation process under the impact of the ultrasonic wave for CO₂ gas. The obtained results demonstrated that the thermal conductivity sensor has 9 and 13 s as a response and recovery durations subsequently which outperforms most of the commercially available CO₂ sensors [65]. The as prepared MWCNTs/ZnO by reflux method at 197 °C in ethylene glycol is employed for methanol gas detection. A wide span of temperatures within 100-300 °C was investigated for the sensing behavior where the best performance was gained at the latter

temperature. The Al₂O₃ doped with MWCNTs is also presented for methane detection [66].

6.2.2. Carbon nanotubes/metals for gas sensing:

Carbon nanotubes decorated with gold nanoparticles are examined for (NO₂, CO, and C₆H₆) contaminants detection through a combination of experimental/theoretical routes. Gold nanoparticles depict a direct impact on NO₂, and CO detection, where no significant effect was noticed in C₆H₆. This behavior discrepancy can be clarified by recognizing the connection between the change of resistance (macroscopic property) and Fermi level shift (microscopic feature) after gas adsorption [67]. Additionally, to these materials carbon nanotubes were decorated with rhodium nanoparticles and served as a sensor for the detection of f NO₂, C₂H₄, CO, C₆H₆. Oxygen existence is crucial for the enhancement of gas response because the oxygenated vacancies behave as active adsorption locations for gases and as anchoring sites for rhodium nanoparticles. Additionally easier charge transmission between rhodium nanoparticles and carbon nanotubes can be achieved [68]. Sharafeldin et al., decorated the MWCNTs with Cu, Pt, Ti, Ru and Ag to investigate its gas sensing behavior. They found that the MWCNTs/Cu nanocomposites exhibited the highest sensitivity of 1.75% when exposed to 10ppm H₂S. Also they demonstrated that the MWCNTs/Pt exhibited a greater response of 1.96 % during exposure to 10 ppm NO₂[69]. The zigzag MWCNTs coated with Pd and Pt nano particles were exposed to different concentrations of CO and NO at room temperature. This novel structure was studied employing first-principles calculations. The deep analysis showed that the Pt decorated SWCNTs are more sensitive to CO while, the SWCNTs decorated with Pd is highly sensitive to NO [70]. The Au nanoparticles with controlled size and ratio was developed over MWCNTs to establish an NO₂ gas sensor to detect minor concentration of down to sub ppm level. This study concluded that the deposited amount of Au nano particles control the sensing capabilities. The low Au loading, the heights response toward H₂S [71]. Khan et al., was utilized the simple and cost-effective spray method for depositing Ag/CNTs and ZnO/Ag/CNTs over a cellulose paper. They demonstrated that the Ag/CNTs sensor responded selectively for acetone faster CNTs/ZnO/Ag sensor [72]. The CNTs functionalized with Ni nanoparticles was adapted to detect SO₂, H₂S, and SO₂F₂. Y. Gui et al., reported that the low detection limit (LOD) of the Ni/CNTs sensor was 1 ppm against SF₆. They demonstrated

that the sensitivity toward different gases in the following order H₂S > SOF₂ > SO₂ > SO₂F₂. [73]

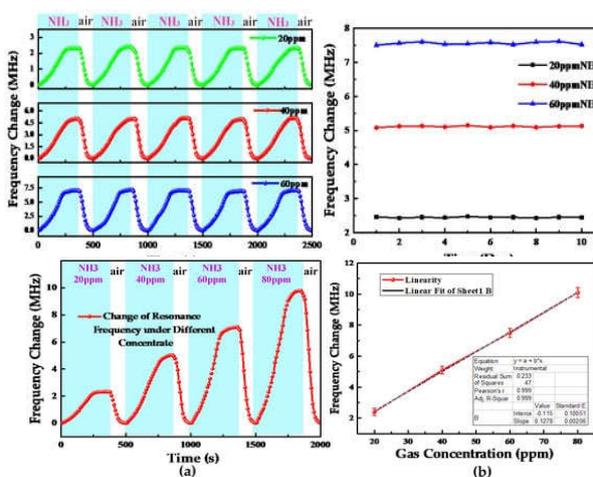


Figure 7: CNTs/Fe₃O₄ gas sensor a) repeatability, b) Stability, c) response at different concentration, and d) linearity, [63]CC BY 4.0

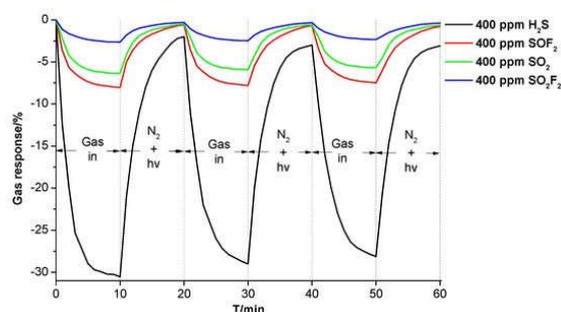
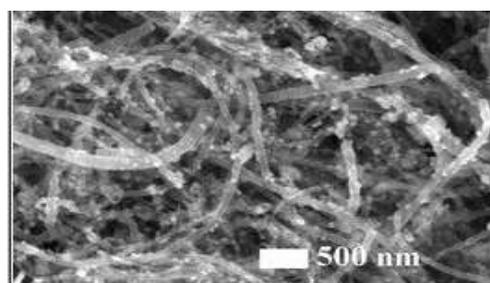


Figure 8:a) HRTEM of CNTs decorated with Ni nano particles and b) the response of CNTs/Ni sensor toward different gases. This figure is obtained from [74] CC BY 4.0

6.2.3. Carbon nanotubes/ organic materials for gas sensing

CNTs/Poly-ethylene glycol composite was used as gas sensors to detect volatile organic compounds (VOCs). Reachable high response (≈ 110 s) and recovery (≈ 152 s) rates were acquired in diverse concentrations of acetone, ethanol, isopropanol and isoprene at ambient temperature. These rates

nominate the sensor as a portable electronic-nose device [75]. Gas sensing can also be promoted based on poly (3,4-ethylenedioxythiophene) polystyrene sulfonate – multiwall carbon nanotubes (PEDOT: PSS-MWCNTs) as the sensitive material. This work targets the development of a low-cost communicating sensor that attain the possibility of sensing platform integration devoted to low power applications as well as the Internet of Things (IoT) [76]. Gas sensing of NO₂ is utilized based on single walled nanotubes mounted on polytetrafluoroethylene (PTFE) filter flexible substrates. A demonstrated stability of sensitivity was depicted during repeated bending of the substrates within 0.75–2 ppm concentrations. However, for 3–5 ppm concentration, a remarkable rise in the sensitivity was achieved. This can be linked to the porous nature of the substrates. Compared with the sensors fabricated over a silicon substrate, duplication of sensitivity can be obtained. Moreover, a decrease of the sensitivity at 10 % and 30 % humidity because of the electron donor nature of water molecules. These results are beneficial for flexible electronics and for monitoring air quality [77].

The detection of ammonia gas is conducted relied on CNTs and polyaniline films. Three different doping routes were performed (i.e. sulfuric acid, camphorsulfonic acid and m-cresol). The optimum sensor response was acquired for the camphorsulfonic acid is comparable with others. This can be regarded to the conservation of polyaniline primary volume, and the well-distributed polarons initiated by this doping agent. This device operates with an optimized sensitivity for ammonia gas detection with a limit of detection of 4 ppm [78]. Chiou et al., demonstrated an acetone gas sensor of polyethylene glycol (PEG)/MWCNTs composite film. The results for sensing performance revealed a higher sensitivity for PEG/MWCNTs in the presence of moderate temperature than the absence of the thermal treatment which is beneficial for environmental applications [79]. W. Zhan et al., explored the efficacy of PANI/CNT composite for the monitoring of NO₂ and NH₃. They improved the sensing performance of PANI/CNT composite via establishing a core-shell structure of p-type MWCNTs and n-type PANI. The low detection limit (LOD) of their structure was attained as 19.6 and 6.5 ppb, for NO₂ and NH₃ respectively as illustrated in fig. 9 [80]

Recently, a variety of 3,4 ethylenedioxythiophene)/poly (4-styrenesulfonate) concentrations were examined for the application of 3D 3,4 ethylenedioxythiophene)/poly (4-styrenesulfonate) (PEDOT: PSS) multi-walled

composite carbon nanotubes in gas sensing, where using ethanol and CO. Enhanced response and recovery times as well as increased conductivity were observed for ethanol and CO. From one side the gas molecules adsorption sites reduced with PEDOT: PSS coating layer, but from the other the charge-carrier transport increases within the multi-walled carbon nanotubes and gas molecules, which is translated finally to a better 3D networking and potential applicability for gas sensing [81].

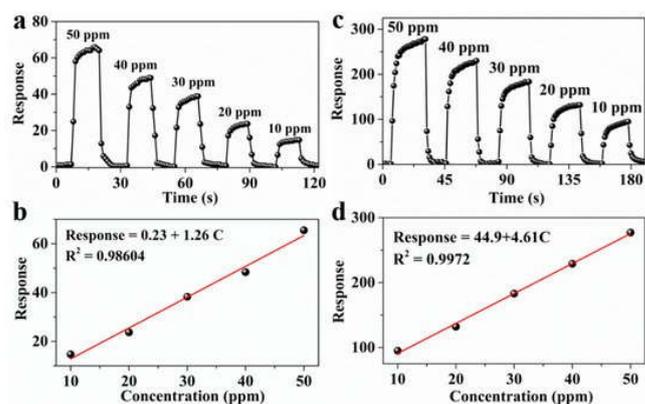


Figure 9:(a) The response of p-PANI/CNT toward NO₂ gas, (b) the fitting curve of sensor p-PANI/CNT against NO₂ concentration, (c) responses of p-PANI/CNT toward NH₃ gas, (d) the fitting curve of sensor p-PANI/CNT against NH₃ concentration, The figure is taken from [80] CC BY 4.0

6.4. Graphene

Graphene is a unique two dimensional material with a honeycomb crystal lattice, introduced initially by Novoselov et al [82], existing in graphite, coal, and created in other means. It owes a distinctive specification such as flexibility, increased surface area, high mobility and mechanical strength, environmental steadiness, versatility, and optical transparency. Even in a vacuum, it maintains high mobility which outcomes Si and Cu. Thanks to the conferred aforementioned properties, graphene is a very promising material for a range of industrial applications, which are engaged in nanotechnological areas as biosensing [83, 84] [85] [86], water treatment [87], photocatalysis and solar cells [88], [89], semiconductors [90] [59], energy storage devices [60], as well as biomedical sector [61] [62]. Moreover, graphene is the standard building block for nanotubes, and 3D graphite. The resulted graphene from graphene oxide reduction differs in structure from pristine graphene. While the former has wrinkled structure owing to lattice defects existence, the latter displays a rippled structure [63]. Graphene can be created by mechanical or chemical

exfoliation. Other processes rely on chemical vapor deposition and other methodologies[64].

6.4.1. Synthesis of graphene

Graphene deserves great attention as it has a large theoretical specific surface area (2630 m²g⁻¹), high intrinsic mobility (200,000 cm² v⁻¹s⁻¹), [65][66] high Young's modulus (*1.0 TPa) [67]and thermal conductivity (5000 Wm⁻¹K⁻¹), [68][69][70][71]optical transmittance (*97.7 %) and good electrical conductivity, on other hand, preparation of the large specific surface area, high quality is not applicable in a low cost-effective way.

Monoatomic or single-layer graphene is called one graphitic layer, also by the same way bilayer graphene contains two graphitic layers, and tri-layer graphene contains three graphitic layers. Few layer graphene referred to more than 5 layers up to 10 layer graphene, and multilayer graphene, nanocrystalline, or thin graphite thick graphene is pointed to *20–30 layer graphene.[72]. for over 40 years graphene has been developed [73–79] and measurements of properties in exfoliated layers [80], of graphene grown on (Si) [81], large-area graphene grown on copper (Cu) substrates [82], as well as different research including the involvement of chemically modified graphene (CMG) to produce novel, and modern materials. [77–86]

Graphene can be synthesized by many methods through mechanical cleaving (exfoliation), chemical exfoliation, chemical synthesis (reduced graphene oxide), and thermal chemical vapor deposition (CVD), which are the most generally used nowadays. A flowchart of graphene preparation techniques is obtained in Fig.10.

6.3.1.1. Mechanical exfoliation

Mechanical exfoliation is the most extraordinary and prominent technique for preparing single-layer graphene. Graphene synthesis can be synthesized through mechanical exfoliation as the first method used. mechanical exfoliation is a top-down technique, by which linear or transverse stress is generated on the surface of the flaked structure materials.

For mechanical exfoliation, the external force required to separate one mono-atomic layer from graphite is 300 nN/cm². [87]

Actually various thicknesses of graphene flakes could be created by mechanical exfoliation or exfoliating sheets from graphitic materials like highly ordered pyrolytic graphite (HOPG), natural graphite, or single-crystal graphite [88][89][90][78][91][92]

This exfoliation can be performed by different types of agents such as scotch tape [80], ultra sonication, [93]electric field [94],and even by transfer printing technique, [95][96],etc.

In this micromechanical exfoliation method, graphene is separated from a graphite crystal using adhesive tape.

Actually it is not easy to obtain larger amounts of graphene by this exfoliation method, not even taking into account the lack of sustainable flakes. The difficulty of this method is low, nevertheless, the graphene flakes require to be found on the substrate surface, which is labor exhaustive. The quality of the prepared graphene is very high with almost no defects. Still, the mechanical exfoliation method needs to be enhanced further for large-scale, defect-free, high-purity graphene for mass production in the field of nanotechnology.

6.3.1.2. Chemical exfoliation

The chemical method is one of the best appropriate methods for the synthesis of graphene[130]. In chemical method producing colloidal suspension which modifies graphene from graphite and graphite intercalation compound. Different types of paper-like material [85][97][98][99][100][101]polymer composites,[83] energy storage materials [102]and transparent conductive electrodes [103]have already used chemical methods for production of graphene. Chemical exfoliation is a two-step process. At first, reduces the interlayer van der Waals force to increase the interlayer spacing. Thus it forms graphene intercalated compounds (GICs) [104]. Then it exfoliates graphene with a single to few layers by rapid heating or sonication as schematically represented in fig. 11.

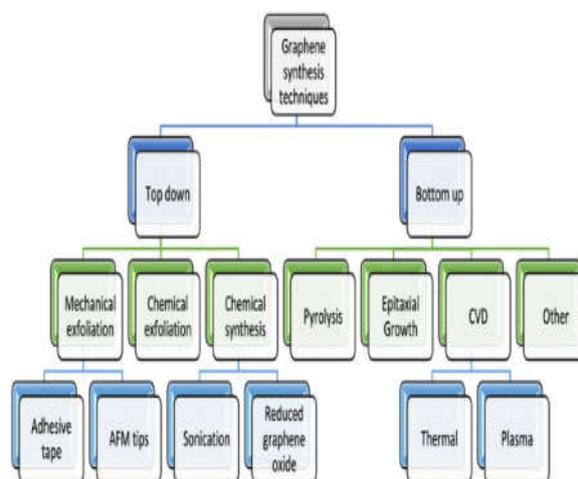


Figure 10: an overview of the most common routes for the graphene preparation methods, source[119] CC BY 4.0

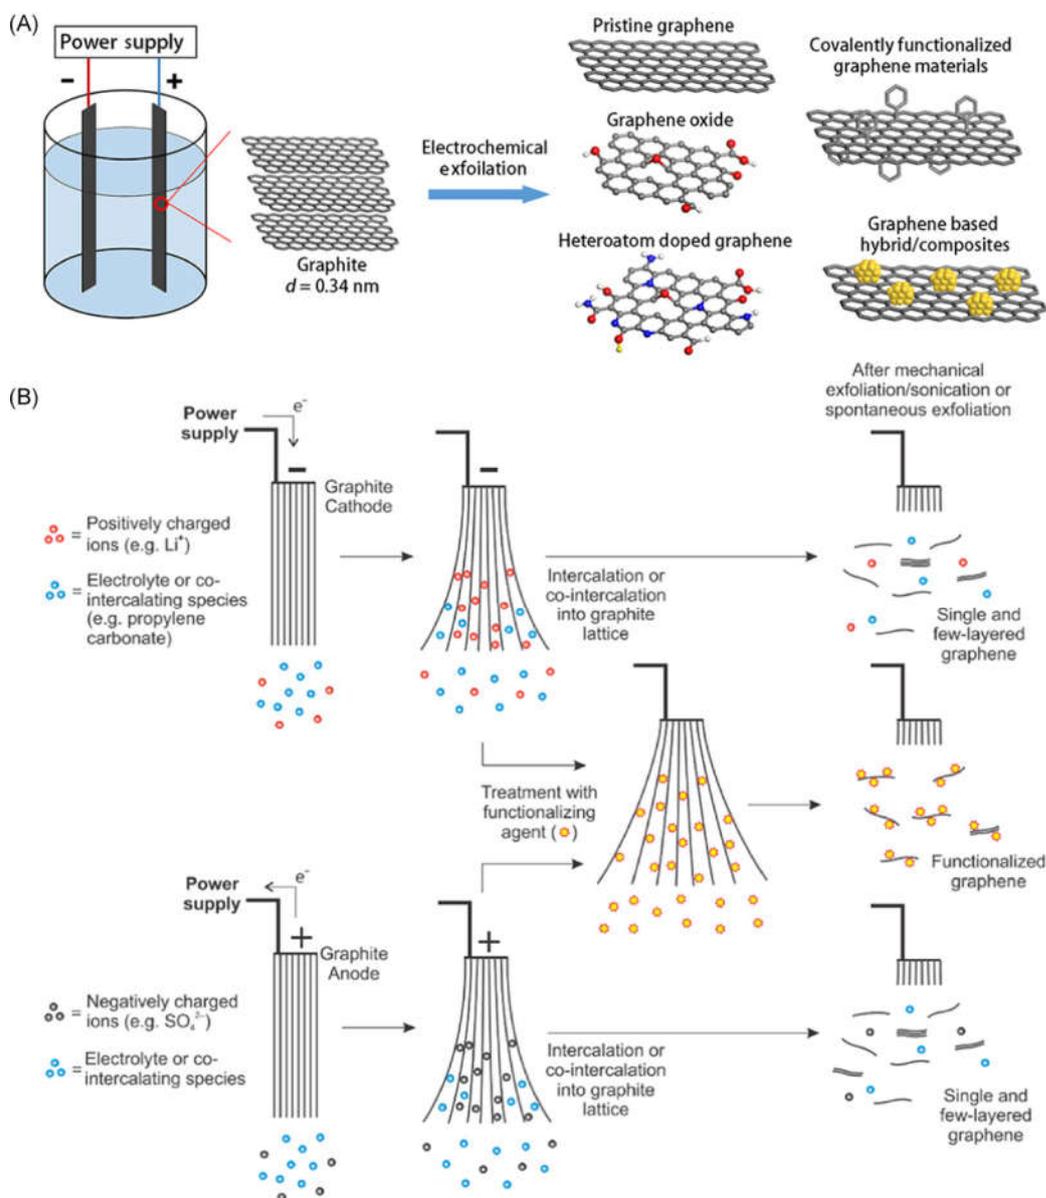


Figure 11: The representation of the chemical exfoliation of the graphene, source: [139] CC BY 4.0

6.3.1.3. Pyrolysis of graphene

One of the chemical methods for the synthesis of graphene in the bottom-up process was the solvothermal method. The molar ratio of sodium and ethanol was 1:1 in a closed vessel in this thermal reaction

Graphene sheets could be in a smooth way pyrolyzed of sodium ethoxide using sonication. These graphene sheets were produced with dimensions of up to $10 \mu\text{m}$. The crystalline structure,

different layers, graphitic nature, band structure were established by TEM and Raman spectroscopy [105].

The benefits package of the pyrolyzation were low-cost and easily fabricated of high-purity, functionalized graphene at low temperature. Yet, the modality of graphene sheets was still not suitable because it comprised a large number of imperfections.

6.3.1.4. Epitaxial growth of graphene

Epitaxial thermal growth on a single crystalline silicon carbide (SiC) surface is one of the most praised methods of graphene synthesis. The schematic representation of the process is depicted in fig. 12. Silicon carbide (SiC) was first used in electrical measurements of patterned epitaxial graphene [80]. Epitaxial graphene growth on SiC has been visualized as a very promising method for large-scale production and commercialization of graphene for applications into electronics. Graphene on SiC produces high-frequency electronics [106], light-emitting devices [106], and radiation hard devices [106]. Top gated transistors have been fabricated from graphene on SiC on a wafer-scale [107]. High-frequency transistors have also been revealed with 100 GHz cut-off frequency [143], higher than state-of-the-art Si transistors of the same gate length. Graphene on SiC has been established as a novel resistance standard based on the quantum Hall effect (QHE) [109][82]. Though this process is very expensive.

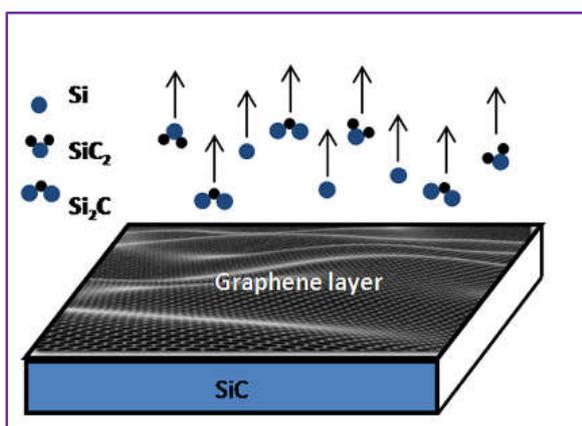


Figure 12: The epitaxial growth of graphene on SiC substrate, source: [145], CC BY 4.0

6.3.1.5. Chemical vapor deposition (CVD)

The deposition of high-quality graphene from the CVD process is usually done onto various transition-metal substrates like Ni [110] Pd [98], Ru [111], Ir [112], and Cu [113]. CVD growth of graphene has been mainly practiced on copper [113][114] and nickel [113][110] substrates. Nickel was the first substrate on which CVD growth of large-area graphene was attempted. These efforts had begun right from 2008. [115].

Different hydrocarbons such as methane, ethylene, acetylene, and benzene were decomposed on various transition metal substrates such as Ni, Cu, Co, Au,

and Ru [113]. Single crystals using an ethylene precursor were found to yield graphene structurally coherent even over the Ir step edges [112].

Depending on the material quality, precursors, width, and the structure required; there are many various types of CVD processes: thermal, plasma enhanced (PECVD), cold wall, hot wall, reactive, and so on.

In CVD process reactors like hot-wall reactor, there temperature is relatively constant everywhere and these walls never get heated in the cold wall systems. Graphene is formed on Cu thin film mostly by cold wall system.

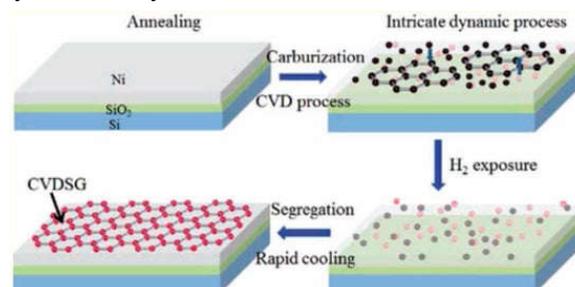


Figure 13: The elucidation of the CVD growth of graphene, source:[152] CC BY 4.0

6.4.2. Graphene/ polymers for gas sensing:

The monitoring and detection of nitrogen dioxide were utilized by employing the rGO/polymer nanofibers. Room temperature applicability and high sensitivity of 1.03 ppm were feasibly acquired. Moreover, 150 ppm detection limit was achieved, synthesis methodology using electro-spun offers a feasible, eco-friendly and robust route for preparation [116]. The acquisition of ammonia sensors was proposed relied on the rGO/ conductive polymers combination through the Langmuir-Schaefer (LS) procedure. The implication of exploiting pyrrole (Py) as the reducing agents demonstrated the highest sensitivity for pyrrole-rGO-polyaniline amongst the four synthesized samples. A detection limit of 0.2 ppm was maintained [117]. Graphene/ethyl cellulose nanocomposite was introduced for the highly sensitive wearable gas sensor with reduced strain response, this sensor displays 0.3% comparative resistance variation at the smallest bending radius of 3.18 mm after 400 bending cycles. For a bending radius of 5 mm, 0.2 % resistance change was grasped. Detection limits range from 37 to 167 ppm was also monitored. The detection of ethanol, acetone, IPA, and hexane were reported [118].

6.4.3. Graphene / metal oxide nanocomposite for gas sensing:

Metal oxides like ZnO, MnO₂, WO₃, MoO₃ and CuO are broadly investigated for sensing applications [119][120][121][55][159][45], from one side they have raised specific area for the surface and decent flexibility [122] from the other side they lack the satisfactory electrical conductivity. The gathering of graphene and its derivatives with the metal oxides can inherently enhance the electrical conductivity and the sensing performances subsequently. The introduction of graphene/metal oxide is reported [123]. The incorporation of metal oxides onto graphene results in emerged physical and chemical specifications. Moreover it possesses a vital role in the suppression of graphene sheets of aggregation [54]. The nanocomposite of NiO/ rGO was introduced for the detection and sensing of methane through the hydrothermal method. The probable mechanism of sensing was credited to the Fermi energy band among NiO nanoparticles and rGO sheets. High response times of approximately 6-18s were noticed for 100-500 ppm concentrations [124]. The detection of formaldehyde is pursued relied on another metal oxide (i.e. ZnO)-rGO nanocomposite by Weiwei Guo et al., where the ZnO was doped by Fe and the nanocomposite was prepared via a one-pot hydrothermal route. The incorporation of Fe onto the ZnO-rGO nanocomposite results in a reduction in the ZnO hexagonal prism accompanied by an elevation of the surface area for the aforementioned ZnO. A ratio of 5 % doping of Fe sensing performance maintains a response-recovery times of 34, 37 seconds for 12-5 ppm concentration of formaldehyde [125]. The same ZnO modified with rGO is employed for the ultrasensitive monitoring of NO₂ gas. Seven-fold enhancement of the response compared to pristine ZnO at 100 °C is approached. Detection limit as low as 5ppm is attained. The elevated performance of the sensor is regarded to the existence of p-n heterojunctions amongst the rGO and ZnO [126]. The hydrothermal method for preparation was introduced to acquire the rGO-TiO₂ nanocomposite with the objective of ammonia sensing. The mentioned nanocomposite demonstrated enhanced selectivity and sensitivity for ammonia concentration down to 5 ppm at room temperature [127]. While the same nanocomposite (rGO-TiO₂ nanocomposite) can detect the CO gas for reduced 100 ppm concentrations [128]. Vardan Galstyan et al., fabricated the rGO/ZnO nanocomposite for detecting NO₂, H₂ and CH₄ gases. the incorporation of rGO enhances the conductivity of the resultant composite, thereby promoting the response to NO₂, and H₂ gases as shown in fig. 14. compared to pure ZnO, the

rGO/ZnO nanocomposite responds selectively to NO₂, gas at relatively low working temperature [167]

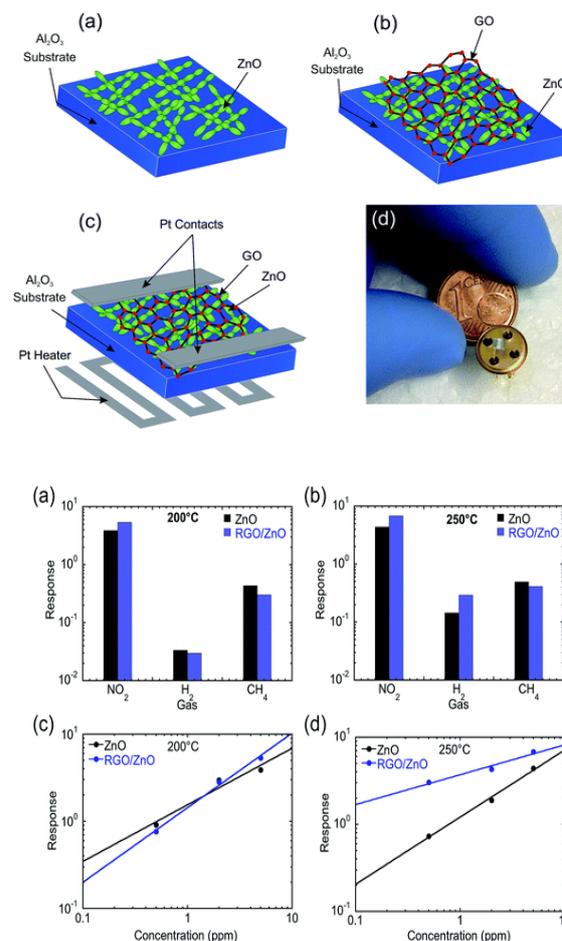


Figure 14: The schematic representation of gas sensor device fabrication. Ref. [167] open access

The detection of another gas (NO₂ in this case), is demonstrated using GO-WO₃ nanocomposite films. The synthesis was performed by a combination of the polyol process and metal-organic decomposition. Imminent sensitivity within 0.5–5 ppm with nice reproducibility was affirmed. Long-term stability for more than a month is reported at room temperature [129]. The decoration of copper oxide with reduced graphene oxide was exploited for carbon monoxide sensing through the layer-by-layer self-assembly methodology. A spacious range of 0.25 ppm to 1000 ppm CO concentration was investigated. Excellent performance for reproducibility, sensitivity, and stability was demonstrated, which originated from the formulated heterojunction at the CuO-rGO interface [130]. The hybrid nanocomposite of SnO₂ and GO revealed recognized sensitivity to detect NH₃ with 10 to 50 ppm at ambient temperature [131]. The carbon

monoxide sensing is also attained using the rGO-Fe₃O₄ nanocomposite, the response-recovery timings of 32-35 s are acquired respectively for 5 ppm concentration[132]. Another type of CO gas sensing for NiO/graphene using the hydrothermal reflux method was introduced[133]. The composites of nitrogen doping onto graphene decorated with MnO₂ was prepared by a means of microwave-assisted procedure. The microwave irradiation facilitated the development of nanoflowers because of the inherent interactions amongst the alternation current and the electric dipoles[134]. The tin oxide modified reduced graphene oxide (SnO₂-rGO) nanocomposite was prepared through one-step hydrothermal procedure for the monitoring of H₂S and SOF₂. The optimal conditions outcoms the pristine rGO sensors. Acquired elevated responses of (34.31% and -3.13%) higher than tan those (5.97% and -1.45%) of pristine rGO sensor at 125 °C, for 100 ppm H₂S and 10 ppm SOF₂, concentrations correspondingly[135]. A Tri-structure system of rGO-SnO₂-Au was effectively synthesized to detect the formaldehyde. Remarkable higher sensor response and selectivity could be attained. This enhanced response might be attributed to the fact of ohmic contact synergistic effect between SnO₂ and rGO, as well as the increased surface area, and Au nanoparticles catalytic effect. [136].

6.4.4. Graphene / metals nanocomposite for gas sensing

Graphene-noble metal gas sensing was also introduced earlier [137][138] Recently, GO- metals are of great interest thanks to their enhanced catalytic, electronic and optical specifications[139]. The hydrogen gas sensing is performed using the Pt-Pd/rGO. Stability and repeatability for the response are confirmed. This might be attributed to the carrier donation and the expansion in the crystal lattice during hydrogenation and dehydrogenation. The response can be enhanced by increasing the hydrogen concentration or reducing the operating temperature. The flow rate alteration doesn't reflect any noticeable changes in the sensor outcome. Upon employing nitrogen instead of air as a gas carrier, higher response/recovery durations were acquired. This might be regarded to the contribution of oxygen in the reaction[140]. NO₂ sensing is also recalled by introducing the impact of electron beam irradiation for Pd-fortified rGO composites. Altered doses of irradiation were executed from 0 to 500 kGy, where the latter dose demonstrates the optimum response. The response time of 345 s was acquired for a 10 ppm concentration of NO₂, while the recovery time hits 816 s for the same concentration and dose. Oxygen functional groups abundance along

with high energy defects initiates this elevated gas response[141].

Pd/rGO hybrid, is used to sense the hydrogen gas. The hybrid was synthesized via microwave irradiated assisted route. Sensing performance was investigated through a spacious temperature range- from room temperature to 120 °C. The highest response of 14.5 % was achieved for 1 % H₂ sensing at 100 °C. this remark might be attributed to the raised amount of hydrogen molecules that interact with the sensing layer[142]. Ammonia gas is also detected using the rGO samples decorated by Ag, Au, and Pt nanocomposites synthesized by a single-step chemical reduction process. Amongst these three nanoparticles, silver demonstrated the highest recovery, response, and sensitivity [143]. In recent work, the detection of NO₂ employing Au ornamented porous structure graphene was achieved at the normal room temperature. The sensor maintains a response to diminished gas concentrations as low as 50×10⁻⁹ within 30 s. Au decoration elevated the sensitivity to ~1.5 times higher than pristine graphene[144]. The use of the ternary composite of Ag-MoSe₂/reduced graphene oxide (rGO) for H₂S gas sensing, where the composite was fabricated by following the hydrothermal process. The investigation of varied concentrations 0.1 ppm–30 ppm at room temperature was performed. The loading of Ag onto the compound has an apparent impact, which was regarded to the modulation of the potential barrier during electrons transfer, as well as the synergistic consequences of the ternary composite structure[145].

6.4.5. Graphene / CNTs/ Metal oxide nanocomposites

The nanocomposite of the graphene derivatives and carbon nanotubes mixed with metal oxide for usage in gas sensing applications is also investigated[185]. In addition to these composites carbon nanotubes/ reduced graphene oxide NO₂ gas sensors are introduced. These sensors are supported by flexible polyamide substrate and operated at room temperature. These sensors are remarked with high sensitivity and high bending ability, where the former is due to CNTs array existence and the latter is regarded to the excellent flexibility of graphene films [146].

M. Morsy et al., recently reported that the mentioned nanocomposite incorporated with ZnO acquired by the conventional precipitation procedure benefits in the detection of ammonia gas at room temperature. Increased response and recovery times were noticed for the detected gas under investigation[147]. Inherently, the

graphene/SnO₂ prepared using the sol-gel method has a better gas sensing response than the graphene/MWCNTs/SnO₂ at room temperature for NO₂ as reported by Vibha Srivastava et al. The composite is signified by a reduced time of response < 1 min, and almost 5 min for the recovery period. The raised response can be regarded to the full exposure of the surface towards the surrounding environment [188].

6.4.6. Three-dimensional graphene and graphene foam.

The three-dimensional (3D) graphene foams [148] are introduced as well for different application areas such as Li batteries [149], photocatalysis [150] water treatment [151] and else [152][153]. The freeze-drying (FD) procedure is used to produce 3D graphene nanoplatelets (GNP) foam. This method introduces better mechanical specifications which outcoms the CVD graphene foam. However, it possesses 0.5 times thermal diffusivity because of due to the pore architecture and defects in GNP particles [154]. The detection of glucose is also introduced using graphene foam based as an electrochemical sensing approach. Macroporous 3D graphene foam synthesized by chemical vapor deposition (CVD) helped as the electrode scaffold. The reduced detection limit of 1.5 μM is obtained within a spacious linear range (5–65 μM) [155]. In another report, the macro graphene foam-like is employed for the detection of gases. Herein the combination between the high sensitivity and appropriate reliability. Few ppm levels were attained for the NH₃ and NO₂ gases detection in the air at the ambient situation. Furthermore, the proposed combination attains a desirable mechanical strength and flexibility as well as reduced power consumption regarded to Joule-heating which opposes chemisorbed molecules from the surface of the foam [156]. The 3D reduced graphene oxide (3DRGO) decorated with ZnO nanoparticles was investigated to detect the CO gas. The studied performed by N. HaiHa et al., confirmed the 3DRGO/ZnO composite based gas sensor has a fast response and recovery, good linearity, stability, and enhanced selectivity [198]. The detection of VOCs was executed by 3D graphene loaded with Co₃O₄. The GF/Co₃O₄ nanocomposite exhibited a high response and fast response time toward Xylene at low concentrations [199].

Conclusion:

In this review article, we have surveyed the gas sensing implications for versatile carbon-based nanomaterials. Initially, we have started with an

introduction which presents carbon nanohorns and nanooxions, subsequently heading to nanodiamonds, and carbon quantum dots. At the end of this section, we finish with the carbon nanotubes (CNTs). In the second section, the research progress for CNTs versatile combinations is inherently explored. Herein, the gas sensing performance and evolution for CNTs/metal oxides, CNTs/metals, and CNTs/organic materials highlighting the enhanced detection limits and response/recovery timings are included. Thirdly, we shed lights on the graphene synthesis protocols such as mechanical and chemical exfoliation as well as chemical vapor deposition (CVD). Finally, we investigate graphene combinations for gas sensing. This comprises graphene/metal oxide, graphene/noble metals, and graphene/CNTs/metal oxide. The propagation of the discussion from 0D, 1D to 2D and ending with 3D foam graphene is involved. This gas sensing review delivers the keypoints for the selection of the appropriate carbon-based materials and the accompanying implications needed for the next era of technological and industrial applications.

References

1. Comisso, N., Berlouis, L.E.A., Morrow, J., Pagura, C.: Changes in hydrogen storage properties of carbon nano-horns submitted to thermal oxidation. *International Journal of Hydrogen Energy*. 35, 9070–9081 (2010). <https://doi.org/10.1016/j.ijhydene.2010.06.034>
2. Georgakilas, V., Perman, J.A., Tucek, J., Zboril, R.: Broad Family of Carbon Nanoallotropes: Classification, Chemistry, and Applications of Fullerenes, Carbon Dots, Nanotubes, Graphene, Nanodiamonds, and Combined Superstructures. *Chemical Reviews*. 115, 4744–4822 (2015). <https://doi.org/10.1021/cr500304f>
3. Zhu, S., Xu, G.: Single-walled carbon nanohorns and their applications. *Nanoscale*. 2, 2538–2549 (2010). <https://doi.org/10.1039/c0nr00387e>
4. Zhu, S., Zhang, J., Zhao, X. en, Wang, H., Xu, G., You, J.: Electrochemical behavior and voltammetric determination of L-tryptophan and L-tyrosine using a glassy carbon electrode modified with single-walled carbon nanohorns. *Microchimica Acta*. 181, 445–451 (2014). <https://doi.org/10.1007/s00604-013-1138-9>
5. Mercatelli, L., Sani, E., Giannini, A., Di Ninni, P., Martelli, F., Zaccanti, G.: Carbon nanohorn-based nanofluids: Characterization of the spectral scattering albedo. *Nanoscale Research Letters*. 7, 1–5 (2012). <https://doi.org/10.1186/1556-276X-7-96>

6. Liu, Y., Brown, C.M., Neumann, D.A., Geohegan, D.B., Poretzky, A.A., Rouleau, C.M., Hu, H., Styers-Barnett, D., Krasnov, P.O., Yakobson, B.I.: Metal-assisted hydrogen storage on Pt-decorated single-walled carbon nanohorns. *Carbon*. 50, 4953–4964 (2012). <https://doi.org/10.1016/j.carbon.2012.06.028>
7. Chen, D., Wang, C., Jiang, F., Liu, Z., Shu, C., Wan, L.J.: In vitro and in vivo photothermally enhanced chemotherapy by single-walled carbon nanohorns as a drug delivery system. *Journal of Materials Chemistry B*. 2, 4726–4732 (2014). <https://doi.org/10.1039/c4tb00249k>
8. Miyawaki, J., Yudasaka, M., Imai, H., Yorimitsu, H., Isobe, H., Nakamura, E., Iijima, S.: In vivo magnetic resonance imaging of single-walled carbon nanohorns by labeling with magnetite nanoparticles. *Advanced Materials*. 18, 1010–1014 (2006). <https://doi.org/10.1002/adma.200502174>
9. Sandanayaka, A.S.D., Ito, O., Zhang, M., Ajima, K., Iijima, S., Yudasaka, M., Murakami, T., Tsuchida, K.: Photoinduced electron transfer in zinc phthalocyanine loaded on single-walled carbon nanohorns in aqueous solution. *Advanced Materials*. 21, 4366–4371 (2009). <https://doi.org/10.1002/adma.200901256>
10. Dai, H., Yang, C., Ma, X., Lin, Y., Chen, G.: A highly sensitive and selective sensing ECL platform for naringin based on β -Cyclodextrin functionalized carbon nanohorns. *Chemical Communications*. 47, 11915–11917 (2011). <https://doi.org/10.1039/c1cc14611d>
11. Suehiro, J., Sano, N., Zhou, G., Imakiire, H.: Application of dielectrophoresis to fabrication of carbon nanohorn gas sensor. 64, 408–415 (2006). <https://doi.org/10.1016/j.elstat.2005.11.001>
12. Sano, N., Kinugasa, M., Otsuki, F.: Gas sensor using single-wall carbon nanohorns. *Advanced Powder Technology*. 18, 455–466 (2007). <https://doi.org/10.1163/156855207781389447>
13. Serban, B.C., Buiu, O., Dumbravescu, N., Cobianu, C., Avramescu, V., Brezeanu, M., Bumbac, M., Nicolescu, C.M.: Oxidized Carbon Nanohorns as Novel Sensing Layer for Resistive Humidity Sensor. *Acta Chimica Slovenica*. 67, 469–475 (2020). <https://doi.org/10.17344/acsi.2019.5415>
14. Kagkoura, A., Tagmatarchis, N.: Carbon Nanohorn-Based Electrocatalysts for Energy Conversion, (2020)
15. Mykhailiv, O., Zubyk, H., Plonska-brzezinska, M.E.: Inorganica Chimica Acta Carbon nano-onions: Unique carbon nanostructures with fascinating properties and their potential applications. *Inorganica Chimica Acta*. 468, 49–66 (2017). <https://doi.org/10.1016/j.ica.2017.07.021>
16. Hiep, T., Mohapatra, D., Mahato, N., Parida, S.: Journal of Industrial and Engineering Chemistry Effect of nitrogen doping on the catalytic activity of carbon nano-onions for the oxygen reduction reaction in microbial fuel cells. *Journal of Industrial and Engineering Chemistry*. 81, 269–277 (2020). <https://doi.org/10.1016/j.jiec.2019.09.014>
17. Zuaznabar-gardona, J.C., Fragoso, A.: Band structure, work function and interfacial diagrams of oxygen-functionalized carbon nano-onions. *Synthetic Metals*. 266, 116434 (2020). <https://doi.org/10.1016/j.synthmet.2020.116434>
18. Yang, J., Zhang, Y., Kim, D.Y.: Electrochemical sensing performance of nanodiamond-derived carbon nano-onions: Comparison with multiwalled carbon nanotubes, graphite nano flakes, and glassy carbon. *Carbon*. 98, 74–82 (2016). <https://doi.org/10.1016/j.carbon.2015.10.089>
19. Guo, J., Wang, X., Xu, B.: One-step synthesis of carbon-onion-supported platinum nanoparticles by arc discharge in an aqueous solution. 113, 179–182 (2009). <https://doi.org/10.1016/j.matchemphys.2008.07.039>
20. Mongwe, T.H., Matsoso, B.J., Mutuma, B.K., Coville, N.J.: Diamond & Related Materials Synthesis of chain-like carbon nano-onions by a flame assisted pyrolysis technique using different collecting plates. *Diamond & Related Materials*. 90, 135–143 (2018). <https://doi.org/10.1016/j.diamond.2018.10.002>
21. Wang, C., Li, D., Lu, Z., Song, M., Xia, W.: Continuous preparation of carbon nano-onions in a non-thermal plasma process. *Materials Letters*. 272, 127808 (2020). <https://doi.org/10.1016/j.matlet.2020.127808>
22. Dhonge, B.P., Motaung, D.E., Liu, C., Li, Y., Mwakikunga, B.W.: Sensors and Actuators B: Chemical Nano-scale carbon onions produced by laser photolysis of toluene for detection of optical, humidity, acetone, methanol and ethanol stimuli. *Sensors & Actuators: B. Chemical*. 215, 30–38 (2015). <https://doi.org/10.1016/j.snb.2015.03.033>
23. Mahor, A., Singh, P.P., Bharadwaj, P., Sharma, N., Yadav, S., Rosenholm, J.M., Bansal, K.K.: Carbon-Based Nanomaterials for Delivery of Biologicals and Therapeutics: A Cutting-Edge Technology, (2021)
24. Zhang, Y., Zhao, J., Du, T., Zhu, Z., Zhang, J., Liu, Q.: A gas sensor array for the simultaneous detection of multiple VOCs. *Scientific Reports*. 7, 1960 (2017). <https://doi.org/10.1038/s41598-017-02150-z>
25. Zhang, Y., Yop, K., Hui, D., Park, S.: A critical review of nanodiamond based nanocomposites: Synthesis, properties and

applications. *Composites Part B*. 143, 19–27 (2018). <https://doi.org/10.1016/j.compositesb.2018.01.028>

26. Jariwala, D.H., Patel, D., Wairkar, S.: Materials Science & Engineering C Surface functionalization of nanodiamonds for biomedical applications. *Materials Science & Engineering C*. 113, 110996 (2020). <https://doi.org/10.1016/j.msec.2020.110996>

27. Gao, Y., Yin, P.: Diamond & Related Materials Determination of crystallite size of nanodiamond by Raman spectroscopy. *Diamond & Related Materials*. 99, 107524 (2019). <https://doi.org/10.1016/j.diamond.2019.107524>

28. Iqbal, S., Shahid, M., Zahid, M., Bashir, S., Ashfaq, M., Ahmad, R.: Materials Science in Semiconductor Processing Impact of carrier gas flow rate on the synthesis of nanodiamonds via microplasma technique. *mssp*. 74, 31–41 (2018). <https://doi.org/10.1016/j.mssp.2017.10.002>

29. Mochalin, V.N., Shenderova, O., Ho, D., Gogotsi, Y.: The properties and applications of nanodiamonds. *Nature Nanotechnology*. 7, 11–23 (2012). <https://doi.org/10.1038/nnano.2011.209>

30. Huang, B.-R., Kathiravan, D., Saravanan, A., Mai, P.-H.: Crystalline Nanodiamond-Induced Formation of Carbon Nanotubes for Stable Hydrogen Sensing. *ACS Applied Nano Materials*. 4, 2840–2848 (2021). <https://doi.org/10.1021/acsanm.0c03454>

31. Liu, L., Mi, Z., Guo, Z., Wang, J., Feng, F.: A label-free fluorescent sensor based on carbon quantum dots with enhanced sensitive for the determination of myricetin in real samples. *Microchemical Journal*. 157, 104956 (2020). <https://doi.org/10.1016/j.microc.2020.104956>

32. Molaei, M.J.: *Analytical Methods*. 1266–1287 (2020). <https://doi.org/10.1039/c9ay02696g>

33. Wang, R., Li, G., Dong, Y., Chi, Y., Chen, G.: Carbon Quantum Dot-Functionalized Aerogels for NO₂ Gas Sensing. *Analytical Chemistry*. 85, 8065–8069 (2013). <https://doi.org/10.1021/ac401880h>

34. El-shamy, A.G.: Sensors and Actuators : B . Chemical New nano-composite based on carbon dots (C Dots) decorated magnesium oxide (MgO) nanoparticles (CDots @ MgO) sensor for high H₂ S gas sensitivity performance. *Sensors and Actuators: B. Chemical*. 329, 129154 (2021). <https://doi.org/10.1016/j.snb.2020.129154>

35. Chen, W., Li, F., Choon, P., Ye, Y., Whan, T., Guo, T.: Sensors and Actuators B: Chemical Room temperature pH-dependent ammonia gas sensors using graphene quantum dots. *Sensors & Actuators: B. Chemical*. 222, 763–768 (2016). <https://doi.org/10.1016/j.snb.2015.09.002>

36. Guo, K., Xi, B., Wei, R., Li, H., Feng, J., Xiong, S.: Hierarchical Microcables Constructed by CoP @ C ⊂ Carbon Framework Intertwined with Carbon Nanotubes for Efficient Lithium Storage. 1902913, 1–9 (2020). <https://doi.org/10.1002/aenm.201902913>

37. Li, Y., Ye, W., Cui, Y., Li, B., Yang, Y., Qian, G.: A metal-organic frameworks@ carbon nanotubes based electrochemical sensor for highly sensitive and selective determination of ascorbic acid. *Journal of Molecular Structure*. 1209, 127986 (2020). <https://doi.org/https://doi.org/10.1016/j.molstruc.2020.127986>

38. Ghalandari, M., Maleki, A., Haghghi, A., Safdari Shadloo, M., Alhuyi Nazari, M., Tlili, I.: Applications of nanofluids containing carbon nanotubes in solar energy systems: A review. *Journal of Molecular Liquids*. 313, 113476 (2020). <https://doi.org/https://doi.org/10.1016/j.molliq.2020.113476>

39. Negri, V., Pacheco-Torres, J., Calle, D., López-Larrubia, P.: Carbon Nanotubes in Biomedicine BT - Surface-modified Nanobiomaterials for Electrochemical and Biomedicine Applications. Presented at the (2020)

40. Haibat, J., Ceneviva, S., Spencer, M.P., Kwok, F., Trivedi, S., Mohney, S.E., Yamamoto, N.: Preliminary demonstration of energy-efficient fabrication of aligned CNT-polymer nanocomposites using magnetic fields. *Composites Science and Technology*. 152, 27–35 (2017). <https://doi.org/https://doi.org/10.1016/j.compscitech.2017.09.006>

41. Gong, Y., Baik, Y.-J., Li, C.P., Byon, C., Park, J.M., Ko, T.J.: Experimental and modeling investigation on machined surfaces of HDPE-MWCNT polymer nanocomposite. *The International Journal of Advanced Manufacturing Technology*. 88, 879–885 (2017). <https://doi.org/10.1007/s00170-016-8840-9>

42. Loos, M.: Processing of Polymer Matrix Composites Containing CNTs. Presented at the December (2015)

43. Zhao, J., Wei, L., Yang, Z., Zhang, Y.: Continuous and low-cost synthesis of high-quality multi-walled carbon nanotubes by arc discharge in air. *Physica E: Low-Dimensional Systems and Nanostructures*. 44, 1639–1643 (2012). <https://doi.org/10.1016/j.physe.2012.04.010>

44. Chrzanowska, J., Hoffman, J., Ma, A., Mazurkiewicz, M., Kowalewski, T.A.: Synthesis of carbon nanotubes by the laser ablation method: Effect of laser wavelength. 1867, 1860–1867 (2015). <https://doi.org/10.1002/pssb.201451614>

45. Atchudan, R., Perumal, S., Edison, T.N.J.I., Pandurangan, A., Lee, Y.R.: Synthesis and characterization of graphenated carbon nanotubes on IONPs using acetylene by chemical vapor deposition method. *Physica E: Low-dimensional Systems and Nanostructures*. 74, 355–362 (2015). <https://doi.org/https://doi.org/10.1016/j.physe.2015.07.021>
46. Arora, N., Sharma, N.N.: Arc discharge synthesis of carbon nanotubes: Comprehensive review. *Diamond and Related Materials*. 50, 135–150 (2014). <https://doi.org/10.1016/j.diamond.2014.10.001>
47. Sharma, R., Sharma, A.K., Sharma, V.: Synthesis of carbon nanotubes by arc-discharge and chemical vapor deposition method with analysis of its morphology, dispersion and functionalization characteristics. *Cogent Engineering*. 2, 1094017 (2015). <https://doi.org/10.1080/23311916.2015.1094017>
48. Eatemadi, A., Daraee, H., Karimkhanloo, H., Kouhi, M., Zarghami, N., Akbarzadeh, A., Abasi, M., Hanifehpour, Y., Joo, S.W.: Carbon nanotubes: Properties, synthesis, purification, and medical applications. *Nanoscale Research Letters*. 9, 1–13 (2014). <https://doi.org/10.1186/1556-276X-9-393>
49. Su, F., Qiu, X., Liang, F., Tanaka, M., Qu, T., Yao, Y., Ma, W., Yang, B., Dai, Y., Hayashi, K., Watanabe, T.: Preparation of Nickel Nanoparticles by Direct Current Arc Discharge Method and Their Catalytic Application in Hybrid Na-Air Battery, (2018)
50. Sadrolhosseini, A.R.: Laser Ablation Technique for Synthesis of Metal Nanoparticle in Liquid. Presented at the (2019)
51. Jung, H.K., Lee, H.W.: Effect of Catalytic Layer Thickness on Diameter of Vertically Aligned Individual Carbon Nanotubes. *Journal of Nanomaterials*. 2014, 270989 (2014). <https://doi.org/10.1155/2014/270989>
52. Siang, L., Amran, M., Yusoff, M., Binti, S., Rashid, A., Razak, A.: Journal of Industrial and Engineering Chemistry Continuous production of carbon nanotubes – A review. *Journal of Industrial and Engineering Chemistry*. 17, 367–376 (2011). <https://doi.org/10.1016/j.jiec.2011.05.007>
53. Camilli, L.: Advances on Sensors Based on Carbon Nanotubes. 1–17 (2018). <https://doi.org/10.3390/chemosensors6040062>
54. Access, O.: We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists TOP 1 %.
55. Salama, T.M., Morsy, M., Abou Shahba, R.M., Mohamed, S.H., Mohamed, M.M.: Synthesis of Graphene Oxide Interspersed in Hexagonal WO₃ Nanorods for High-Efficiency Visible-Light Driven Photocatalysis and NH₃ Gas Sensing. *Frontiers in Chemistry*. 7, (2019). <https://doi.org/10.3389/fchem.2019.00722>
56. Hua, C., Shang, Y., Wang, Y., Xu, J., Zhang, Y., Li, X., Cao, A.: A flexible gas sensor based on single-walled carbon nanotube-Fe₂O₃ composite film. *Applied Surface Science*. 405, 405–411 (2017). <https://doi.org/https://doi.org/10.1016/j.apsusc.2017.01.301>
57. Kaviyarasu, K., Mola, G.T., Oseni, S.O., Kanimozhi, K., Magdalane, C.M., Kennedy, J., Maaza, M.: ZnO doped single wall carbon nanotube as an active medium for gas sensor and solar absorber. *Journal of Materials Science: Materials in Electronics*. 30, 147–158 (2019). <https://doi.org/10.1007/s10854-018-0276-6>
58. Barthwal, S., Singh, B., Singh, N.B.: ZnO-SWCNT Nanocomposite as NO₂ gas sensor. *Materials Today: Proceedings*. 5, 15439–15444 (2018). <https://doi.org/https://doi.org/10.1016/j.matpr.2018.05.030>
59. Van Duy, N., Van Hieu, N., Huy, P.T., Chien, N.D., Thamilselvan, M., Yi, J.: Mixed SnO₂/TiO₂ included with carbon nanotubes for gas-sensing application. *Physica E: Low-dimensional Systems and Nanostructures*. 41, 258–263 (2008). <https://doi.org/https://doi.org/10.1016/j.physe.2008.07.007>
60. Chimowa, G., Tshabalala, Z.P., Akande, A.A., Bepete, G., Mwakikunga, B., Ray, S.S., Benecha, E.M.: Improving methane gas sensing properties of multi-walled carbon nanotubes by vanadium oxide filling. *Sensors and Actuators B: Chemical*. 247, 11–18 (2017). <https://doi.org/https://doi.org/10.1016/j.snb.2017.02.167>
61. Casanova-ch, J., Navarrete, E., Noifalise, X., Umek, P., Bittencourt, C., Llobet, E.: Gas Sensing with Iridium Oxide Nanoparticle Decorated Carbon Nanotubes. (2019). <https://doi.org/10.3390/s19010113>
62. Septiani, N.L.W., Yulianto, B., Nugraha, Dipojono, H.K.: Multiwalled carbon nanotubes–zinc oxide nanocomposites as low temperature toluene gas sensor. *Applied Physics A*. 123, 166 (2017). <https://doi.org/10.1007/s00339-017-0803-y>
63. Guo, T., Zhou, T., Tan, Q., Guo, Q., Lu, F., Xiong, J.: A Room-Temperature CNT/Fe₃O₄ Based Passive Wireless Gas Sensor, (2018)
64. Dhall, S., Sood, K., Jaggi, N.: A hydrogen gas sensor using a Pt-sputtered MWCNTs/ZnO nanostructure. *Measurement Science and*

- Technology. 25, 85103 (2014). <https://doi.org/10.1088/0957-0233/25/8/085103>
65. Shen, B., Zhang, F., Jiang, L., Liu, X., Song, X., Qin, X., Li, X.: Improved Sensing Properties of Thermal Conductivity-Type CO₂ Gas Sensors by Loading Multi-Walled Carbon Nanotubes Into Nano-Al₂O₃ Powders, <https://www.frontiersin.org/article/10.3389/fenrg.2021.634321>, (2021)
66. Liu, X.-L., Shen, B., Zhang, H.-G., Sun, Y.-Y., Qu, F.: Gas Sensing Properties of Methane Based on Al₂O₃-Doped Multi-Walled Carbon Nanotubes
67. Zanolli, Z., Leghrib, R., Felten, A., Pireaux, J.-J., Llobet, E., Charlier, J.-C.: Gas Sensing with Au-Decorated Carbon Nanotubes. *ACS Nano*. 5, 4592–4599 (2011). <https://doi.org/10.1021/nn200294h>
68. Leghrib, R., Dufour, T., Demoisson, F., Claessens, N., Reniers, F., Llobet, E.: Gas sensing properties of multiwall carbon nanotubes decorated with rhodium nanoparticles. *Sensors and Actuators B: Chemical*. 160, 974–980 (2011). <https://doi.org/https://doi.org/10.1016/j.snb.2011.09.014>
69. Sharafeldin, I., Garcia-Rios, S., Ahmed, N., Alvarado, M., Vilanova, X., Allam, N.K.: Metal-decorated carbon nanotubes-based sensor array for simultaneous detection of toxic gases. *Journal of Environmental Chemical Engineering*. 9, 104534 (2021). <https://doi.org/https://doi.org/10.1016/j.jece.2020.104534>
70. Li, K., Wang, W., Cao, D.: Metal (Pd, Pt)-decorated carbon nanotubes for CO and NO sensing. *Sensors and Actuators B: Chemical*. 159, 171–177 (2011). <https://doi.org/https://doi.org/10.1016/j.snb.2011.06.068>
71. Dilonardo, E., Penza, M., Alvisi, M., Di Franco, C., Rossi, R., Palmisano, F., Torsi, L., Cioffi, N.: Electrophoretic deposition of Au NPs on MWCNT-based gas sensor for tailored gas detection with enhanced sensing properties. *Sensors and Actuators B: Chemical*. 223, 417–428 (2016). <https://doi.org/https://doi.org/10.1016/j.snb.2015.09.112>
72. Khan, F.U., Ansar, M.T., Ullah, Z., Ali, R., Waseem, M., Mustafa, G.M., Atiq, S., Naseem, S.: Acetone sensing and modeling through functionalized Ag-catalysts and CNTs via low cost metal-organic framework-derived ZnO nanostructures. *Ceramics International*. 47, 3361–3367 (2021). <https://doi.org/https://doi.org/10.1016/j.ceramint.2020.09.180>
73. Study, T.: Ni-CNT Chemical Sensor for SF₆ Decomposition Components Detection: A Combined Experimental and Theoretical Study. (2018). <https://doi.org/10.3390/s18103493>
74. Gui, Y., Zhang, X., Lv, P., Wang, S., Tang, C., Zhou, Q.: Ni-CNT Chemical Sensor for SF₆ Decomposition Components Detection: A Combined Experimental and Theoretical Study, (2018)
75. Liu, Z., Yang, T., Dong, Y., Wang, X.: A room temperature VOCs gas sensor based on a layer by layer multi-walled carbon nanotubes/polyethylene glycol composite. *Sensors (Switzerland)*. 18, 3113 (2018). <https://doi.org/10.3390/s18093113>
76. Bahoumina, P., Hallil, H., Lachaud, J.L., Abdelghani, A., Frigui, K., Bila, S., Baillargeat, D., Ravichandran, A., Coquet, P., Paragua, C., Pichonat, E., Happy, H., Rebière, D., Dejous, C.: Microwave flexible gas sensor based on polymer multi wall carbon nanotubes sensitive layer. *Sensors and Actuators B: Chemical*. 249, 708–714 (2017). <https://doi.org/https://doi.org/10.1016/j.snb.2017.04.127>
77. Agarwal, P.B., Alam, B., Sharma, D.S., Sharma, S., Mandal, S., Agarwal, A.: Flexible NO₂ gas sensor based on single-walled carbon nanotubes on polytetrafluoroethylene substrates. *Flexible and Printed Electronics*. 3, 035001 (2018). <https://doi.org/10.1088/2058-8585/aacc8f>
78. Eising, M., Cava, C.E., Salvatierra, R.V., Zarkin, A.J.G., Roman, L.S.: Doping effect on self-assembled films of polyaniline and carbon nanotube applied as ammonia gas sensor. *Sensors and Actuators B: Chemical*. 245, 25–33 (2017). <https://doi.org/https://doi.org/10.1016/j.snb.2017.01.132>
79. Chiou, J.-C., Wu, C.-C., Lin, T.-M.: Sensitivity Enhancement of Acetone Gas Sensor using Polyethylene Glycol/Multi-Walled Carbon Nanotubes Composite Sensing Film with Thermal Treatment, (2019)
80. Engineering, I.: High-Performance Gas Sensor of Polyaniline / Carbon Nanotube Composites Promoted by. (2019)
81. Kim, H., Jang, Y., Lee, G.W., Yang, S.Y., Jung, J., Oh, J.: Tunable Chemical Grafting of Three-Dimensional Poly (3, 4-ethylenedioxythiophene)/Poly (4-styrenesulfonate)-Multiwalled Carbon Nanotubes Composite with Faster Charge-Carrier Transport for Enhanced Gas Sensing Performance, (2020)
82. Novoselov, K.S., Geim, A.K., Morozov, S. V, Jiang, D., Katsnelson, M.I., Grigorieva, I. V, Dubonos, S. V, Firsov, A.A.: Two-dimensional gas of massless Dirac fermions in graphene. *Nature*. 438, 197–200 (2005). <https://doi.org/10.1038/nature04233>

83. Suvarnaphaet, P., Pechprasarn, S.: Graphene-based materials for biosensors: a review. *Sensors*. 17, 2161 (2017)
84. Nag, A., Mitra, A., Mukhopadhyay, S.C.: Graphene and its sensor-based applications: A review. *Sensors and Actuators A: Physical*. 270, 177–194 (2018)
85. Wang, Z., Shaygan, M., Otto, M., Schall, D., Neumaier, D.: Flexible Hall sensors based on graphene. *Nanoscale*. 8, 7683–7687 (2016). <https://doi.org/10.1039/C5NR08729E>
86. Tian, W., Liu, X., Yu, W.: Research Progress of Gas Sensor Based on Graphene and Its Derivatives: A Review, (2018)
87. Manafi, M.R., Manafi, P., Agarwal, S., Bharti, A.K., Asif, M., Gupta, V.K.: Synthesis of nanocomposites from polyacrylamide and graphene oxide: application as flocculants for water purification. *Journal of colloid and interface science*. 490, 505–510 (2017)
88. Mishra, S., Acharya, R.: Photocatalytic applications of graphene based semiconductor composites: A review. *Materials Today: Proceedings*. (2020). <https://doi.org/10.1016/j.matpr.2020.04.066>
89. Kuhn, L., Gorji, N.E.: Review on the graphene/nanotube application in thin film solar cells. *Materials Letters*. 171, 323–326 (2016)
90. Neumaier, D., Pindl, S., Lemme, M.C.: Integrating graphene into semiconductor fabrication lines. *Nature Materials*. 18, 525 (2019)
91. Yousefi, R., Cheraghizade, M.: Semiconductor/Graphene Nanocomposites: Synthesis, Characterization, and Applications. In: *Applications of Nanomaterials*. pp. 23–43. Elsevier (2018)
92. Li, X., Zhi, L.: Graphene hybridization for energy storage applications. *Chemical Society Reviews*. 47, 3189–3216 (2018). <https://doi.org/10.1039/C7CS00871F>
93. Reina, G., González-Domínguez, J.M., Criado, A., Vázquez, E., Bianco, A., Prato, M.: Promises, facts and challenges for graphene in biomedical applications. *Chemical Society Reviews*. 46, 4400–4416 (2017). <https://doi.org/10.1039/C7CS00363C>
94. Nguyen, B.H., Nguyen, V.H.: Promising applications of graphene and graphene-based nanostructures. *Advances in Natural Sciences: Nanoscience and Nanotechnology*. 7, 23002 (2016). <https://doi.org/10.1088/2043-6262/7/2/023002>
95. Shao, Y., Wang, J., Wu, H., Liu, J., Aksay, I.A., Lin, Y.: Graphene based electrochemical sensors and biosensors: a review. *Electroanalysis: An International Journal Devoted to Fundamental and Practical Aspects of Electroanalysis*. 22, 1027–1036 (2010)
96. Lee, X.J., Hiew, B.Y.Z., Lai, K.C., Lee, L.Y., Gan, S., Thangalazhy-Gopakumar, S., Rigby, S.: Review on graphene and its derivatives: Synthesis methods and potential industrial implementation. *Journal of the Taiwan Institute of Chemical Engineers*. 98, 163–180 (2019). <https://doi.org/https://doi.org/10.1016/j.jtice.2018.10.028>
97. Bolotin, K.I., Sikes, K.J., Jiang, Z., Klima, M., Fudenberg, G., Hone, J., Kim, P., Stormer, H.L.: Ultrahigh electron mobility in suspended graphene. *Solid State Communications*. 146, 351–355 (2008). <https://doi.org/https://doi.org/10.1016/j.ssc.2008.02.024>
98. Morozov, S. V., Novoselov, K.S., Katsnelson, M.I., Schedin, F., Elias, D.C., Jaszczak, J.A., Geim, A.K.: Giant Intrinsic Carrier Mobilities in Graphene and Its Bilayer. *Physical Review Letters*. 100, 16602 (2008). <https://doi.org/10.1103/PhysRevLett.100.016602>
99. Lee, C., Wei, X., Kysar, J.W., Hone, J.: Measurement of the Elastic Properties and Intrinsic Strength of Monolayer Graphene. *Science*. 321, 385 LP – 388 (2008). <https://doi.org/10.1126/science.1157996>
100. Balandin, A.A., Ghosh, S., Bao, W., Calizo, I., Teweldebrhan, D., Miao, F., Lau, C.N.: Superior Thermal Conductivity of Single-Layer Graphene. *Nano Letters*. 8, 902–907 (2008). <https://doi.org/10.1021/nl0731872>
101. Moser, J., Barreiro, A., Bachtold, A.: Current-induced cleaning of graphene. *Applied Physics Letters*. 91, 163513 (2007). <https://doi.org/10.1063/1.2789673>
102. Cai, W., Zhu, Y., Li, X., Piner, R.D., Ruoff, R.S.: Large area few-layer graphene/graphite films as transparent thin conducting electrodes. *Applied Physics Letters*. 95, 123115 (2009). <https://doi.org/10.1063/1.3220807>
103. Li, X., Zhu, Y., Cai, W., Borysiak, M., Han, B., Chen, D., Piner, R.D., Colombo, L., Ruoff, R.S.: Transfer of Large-Area Graphene Films for High-Performance Transparent Conductive Electrodes. *Nano Letters*. 9, 4359–4363 (2009). <https://doi.org/10.1021/nl902623y>
104. Choi, W., Lee, J.: Graphene: synthesis and applications. CRC press (2019)
105. Boehm, H.P., Clauss, A., Fischer, G.O., Hofmann, U.: The adsorption behavior of very thin carbon films. *Z. Anorg. Allg. Chem*. 316, 119–127 (1962)
106. Boehm, H.P., Setton, R., Stumpp, E.: Nomenclature and terminology of graphite intercalation compounds (IUPAC Recommendations 1994): . *Pure and Applied Chemistry*. 66, 1893–1901 (1994). <https://doi.org/doi:10.1351/pac199466091893>

107. Boehm, H.P., Setton, R., Stumpp, E.: Nomenclature and terminology of graphite intercalation compounds, (1986)
108. Wintterlin, J., Bocquet, M.-L.: Graphene on metal surfaces. *Surface Science*. 603, 1841–1852 (2009). <https://doi.org/https://doi.org/10.1016/j.susc.2008.08.037>
109. Van Bommel, A.J., Crombeen, J.E., Van Tooren, A.: LEED and Auger electron observations of the SiC(0001) surface. *Surface Science*. 48, 463–472 (1975). [https://doi.org/https://doi.org/10.1016/0039-6028\(75\)90419-7](https://doi.org/https://doi.org/10.1016/0039-6028(75)90419-7)
110. Lu, X., Yu, M., Huang, H., Ruoff, R.S.: Tailoring graphite with the goal of achieving single sheets. *Nanotechnology*. 10, 269–272 (1999). <https://doi.org/10.1088/0957-4484/10/3/308>
111. Lu, X., Huang, H., Nemchuk, N., Ruoff, R.S.: Patterning of highly oriented pyrolytic graphite by oxygen plasma etching. *Applied Physics Letters*. 75, 193–195 (1999). <https://doi.org/10.1063/1.124316>
112. Novoselov, K.S., Geim, A.K., Morozov, S. V., Jiang, D., Zhang, Y., Dubonos, S. V., Grigorieva, I. V., Firsov, A.A.: Electric field in atomically thin carbon films. *Science*. 306, 666–669 (2004). <https://doi.org/10.1126/science.1102896>
113. Berger, C., Song, Z., Li, T., Li, X., Ogbazghi, A.Y., Feng, R., Dai, Z., Marchenkov, A.N., Conrad, E.H., First, P.N., de Heer, W.A.: Ultrathin Epitaxial Graphite: 2D Electron Gas Properties and a Route toward Graphene-based Nanoelectronics. *The Journal of Physical Chemistry B*. 108, 19912–19916 (2004). <https://doi.org/10.1021/jp040650f>
114. Li, X., Cai, W., An, J., Kim, S., Nah, J., Yang, D., Piner, R., Velamakanni, A., Jung, I., Tutuc, E., Banerjee, S.K., Colombo, L., Ruoff, R.S.: Large-Area Synthesis of High-Quality and Uniform Graphene Films on Copper Foils. *Science*. 324, 1312 LP – 1314 (2009). <https://doi.org/10.1126/science.1171245>
115. Stankovich, S., Dikin, D.A., Dommett, G.H.B., Kohlhaas, K.M., Zimney, E.J., Stach, E.A., Piner, R.D., Nguyen, S.T., Ruoff, R.S.: Graphene-based composite materials. *Nature*. 442, 282–286 (2006). <https://doi.org/10.1038/nature04969>
116. Watcharotone, S., Dikin, D.A., Stankovich, S., Piner, R., Jung, I., Dommett, G.H.B., Evmenenko, G., Wu, S.-E., Chen, S.-F., Liu, C.-P., Nguyen, S.T., Ruoff, R.S.: Graphene–Silica Composite Thin Films as Transparent Conductors. *Nano Letters*. 7, 1888–1892 (2007). <https://doi.org/10.1021/nl070477+>
117. Dikin, D.A., Stankovich, S., Zimney, E.J., Piner, R.D., Dommett, G.H.B., Evmenenko, G., Nguyen, S.T., Ruoff, R.S.: Preparation and characterization of graphene oxide paper. *Nature*. 448, 457–460 (2007). <https://doi.org/10.1038/nature06016>
118. Park, S., Ruoff, R.S.: Chemical methods for the production of graphenes. *Nature Nanotechnology*. 4, 217–224 (2009). <https://doi.org/10.1038/nnano.2009.58>
119. Bhuyan, M.S.A., Uddin, M.N., Islam, M.M., Bipasha, F.A., Hossain, S.S.: Synthesis of graphene. *International Nano Letters*. 6, 65–83 (2016). <https://doi.org/10.1007/s40089-015-0176-1>
120. Zhang, Y., Small, J.P., Pontius, W. V, Kim, P.: Fabrication and electric-field-dependent transport measurements of mesoscopic graphite devices. *Applied Physics Letters*. 86, 73104 (2005). <https://doi.org/10.1063/1.1862334>
121. Hiura, H., Ebbesen, T.W., Fujita, J., Tanigaki, K., Takada, T.: Role of sp³ defect structures in graphite and carbon nanotubes. *Nature*. 367, 148–151 (1994). <https://doi.org/10.1038/367148a0>
122. Ebbesen, T.W., Hiura, H.: Graphene in 3-dimensions: Towards graphite origami. *Advanced Materials*. 7, 582–586 (1995). <https://doi.org/https://doi.org/10.1002/adma.19950070618>
123. Bernhardt, T.M., Kaiser, B., Rademann, K.: Formation of superperiodic patterns on highly oriented pyrolytic graphite by manipulation of nanosized graphite sheets with the STM tip. *Surface Science*. 408, 86–94 (1998). [https://doi.org/https://doi.org/10.1016/S0039-6028\(98\)00152-6](https://doi.org/https://doi.org/10.1016/S0039-6028(98)00152-6)
124. Roy, H.-V., Kallinger, C., Marsen, B., Sattler, K.: Manipulation of graphitic sheets using a tunneling microscope. *Journal of Applied Physics*. 83, 4695–4699 (1998). <https://doi.org/10.1063/1.367257>
125. Ci, L., Song, L., Jariwala, D., Elias, A.L., Gao, W., Terrones, M., Ajayan, P.M.: Graphene Shape Control by Multistage Cutting and Transfer. *Advanced Materials*. 21, 4487–4491 (2009). <https://doi.org/https://doi.org/10.1002/adma.200900942>
126. Liang, X., Chang, A.S.P., Zhang, Y., Harteneck, B.D., Choo, H., Olynick, D.L., Cabrini, S.: Electrostatic Force Assisted Exfoliation of Prepatterned Few-Layer Graphenes into Device Sites. *Nano Letters*. 9, 467–472 (2009). <https://doi.org/10.1021/nl803512z>
127. Liang, X., Fu, Z., Chou, S.Y.: Graphene Transistors Fabricated via Transfer-Printing In

- Device Active-Areas on Large Wafer. *Nano Letters*. 7, 3840–3844 (2007). <https://doi.org/10.1021/nl072566s>
128. Chen, J.-H., Ishigami, M., Jang, C., Hines, D.R., Fuhrer, M.S., Williams, E.D.: Printed Graphene Circuits. *Advanced Materials*. 19, 3623–3627 (2007). <https://doi.org/https://doi.org/10.1002/adma.200701059>
129. Huc, V., Bendiab, N., Rosman, N., Ebbesen, T., Delacour, C., Bouchiat, V.: Large and flat graphene flakes produced by epoxy bonding and reverse exfoliation of highly oriented pyrolytic graphite. *Nanotechnology*. 19, 455601 (2008). <https://doi.org/10.1088/0957-4484/19/45/455601>
130. Alam, M.K., Rahman, M.M., Elzwawy, A., Torati, S.R., Islam, M.S., Todo, M., Asiri, A.M., Kim, D., Kim, C.: Highly sensitive and selective detection of Bis-phenol A based on hydroxyapatite decorated reduced graphene oxide nanocomposites. *Electrochimica Acta*. 241, 353–361 (2017). <https://doi.org/https://doi.org/10.1016/j.electacta.2017.04.135>
131. Park, S., Lee, K.-S., Bozoklu, G., Cai, W., Nguyen, S.T., Ruoff, R.S.: Graphene Oxide Papers Modified by Divalent Ions—Enhancing Mechanical Properties via Chemical Cross-Linking. *ACS Nano*. 2, 572–578 (2008). <https://doi.org/10.1021/nn700349a>
132. Li, D., Müller, M.B., Gilje, S., Kaner, R.B., Wallace, G.G.: Processable aqueous dispersions of graphene nanosheets. *Nature Nanotechnology*. 3, 101–105 (2008). <https://doi.org/10.1038/nnano.2007.451>
133. Xu, Y., Bai, H., Lu, G., Li, C., Shi, G.: Flexible Graphene Films via the Filtration of Water-Soluble Noncovalent Functionalized Graphene Sheets. *Journal of the American Chemical Society*. 130, 5856–5857 (2008). <https://doi.org/10.1021/ja800745y>
134. Park, S., An, J., Piner, R.D., Jung, I., Yang, D., Velamakanni, A., Nguyen, S.T., Ruoff, R.S.: Aqueous Suspension and Characterization of Chemically Modified Graphene Sheets. *Chemistry of Materials*. 20, 6592–6594 (2008). <https://doi.org/10.1021/cm801932u>
135. Chen, H., Müller, M.B., Gilmore, K.J., Wallace, G.G., Li, D.: Mechanically Strong, Electrically Conductive, and Biocompatible Graphene Paper. *Advanced Materials*. 20, 3557–3561 (2008). <https://doi.org/https://doi.org/10.1002/adma.200800757>
136. Stoller, M.D., Park, S., Zhu, Y., An, J., Ruoff, R.S.: Graphene-Based Ultracapacitors. *Nano Letters*. 8, 3498–3502 (2008). <https://doi.org/10.1021/nl802558y>
137. Wang, X., Zhi, L., Müllen, K.: Transparent, Conductive Graphene Electrodes for Dye-Sensitized Solar Cells. *Nano Letters*. 8, 323–327 (2008). <https://doi.org/10.1021/nl072838r>
138. Wu, Y.H., Yu, T., Shen, Z.X.: Two-dimensional carbon nanostructures: Fundamental properties, synthesis, characterization, and potential applications. *Journal of Applied Physics*. 108, 71301 (2010). <https://doi.org/10.1063/1.3460809>
139. Liu, F., Wang, C., Sui, X., Riaz, M.A., Xu, M., Wei, L., Chen, Y.: Synthesis of graphene materials by electrochemical exfoliation: Recent progress and future potential. *Carbon Energy*. 1, 173–199 (2019). <https://doi.org/https://doi.org/10.1002/cey2.14>
140. Choucair, M., Thordarson, P., Stride, J.A.: Gram-scale production of graphene based on solvothermal synthesis and sonication. *Nature Nanotechnology*. 4, 30–33 (2009). <https://doi.org/10.1038/nnano.2008.365>
141. Davis, R.F., Kelner, G., Shur, M., Palmour, J.W., Edmond, J.A.: Thin film deposition and microelectronic and optoelectronic device fabrication and characterization in monocrystalline alpha and beta silicon carbide. *Proceedings of the IEEE*. 79, 677–701 (1991). <https://doi.org/10.1109/5.90132>
142. Kedzierski, J., Hsu, P., Healey, P., Wyatt, P.W., Keast, C.L., Sprinkle, M., Berger, C., Heer, W.A. de: Epitaxial Graphene Transistors on SiC Substrates. *IEEE Transactions on Electron Devices*. 55, 2078–2085 (2008). <https://doi.org/10.1109/TED.2008.926593>
143. Lin, Y.-M., Dimitrakopoulos, C., Jenkins, K.A., Farmer, D.B., Chiu, H.-Y., Grill, A., Avouris, P.: 100-GHz transistors from wafer-scale epitaxial graphene. *Science*. 327, 662 (2010)
144. Schwierz, F.: Graphene transistors. *Nature Nanotechnology*. 5, 487–496 (2010). <https://doi.org/10.1038/nnano.2010.89>
145. Mishra, N., Boeckl, J., Motta, N., Iacopi, F.: Graphene growth on silicon carbide: A review. *physica status solidi (a)*. 213, 2277–2289 (2016). <https://doi.org/https://doi.org/10.1002/pssa.201600091>
146. Kim, K.S., Zhao, Y., Jang, H., Lee, S.Y., Kim, J.M., Kim, K.S., Ahn, J.-H., Kim, P., Choi, J.-Y., Hong, B.H.: Large-scale pattern growth of graphene films for stretchable transparent electrodes. *Nature*. 457, 706–710 (2009). <https://doi.org/10.1038/nature07719>
147. Sutter, P.W., Flege, J.-I., Sutter, E.A.: Epitaxial graphene on ruthenium. *Nature Materials*. 7, 406–411 (2008). <https://doi.org/10.1038/nmat2166>
148. Coraux, J., N'Diaye, A.T., Busse, C., Michely, T.: Structural Coherency of Graphene on

- Ir(111). *Nano Letters*. 8, 565–570 (2008). <https://doi.org/10.1021/nl0728874>
149. Reina, A., Jia, X., Ho, J., Nezich, D., Son, H., Bulovic, V., Dresselhaus, M.S., Kong, J.: Large Area, Few-Layer Graphene Films on Arbitrary Substrates by Chemical Vapor Deposition. *Nano Letters*. 9, 30–35 (2009). <https://doi.org/10.1021/nl801827v>
150. Wei, D., Liu, Y., Wang, Y., Zhang, H., Huang, L., Yu, G.: Synthesis of N-Doped Graphene by Chemical Vapor Deposition and Its Electrical Properties. *Nano Letters*. 9, 1752–1758 (2009). <https://doi.org/10.1021/nl803279t>
151. Obratsov, A.N., Obratsova, E.A., Tyurmina, A. V, Zolotukhin, A.A.: Chemical vapor deposition of thin graphite films of nanometer thickness. *Carbon*. 45, 2017–2021 (2007). <https://doi.org/https://doi.org/10.1016/j.carbon.2007.05.028>
152. Feng, C., Zhu, D., Wang, Y., Jin, S.: Electromechanical Behaviors of Graphene Reinforced Polymer Composites: A Review, (2020)
153. Yuan, W., Huang, L., Zhou, Q., Shi, G.: Ultrasensitive and Selective Nitrogen Dioxide Sensor Based on Self-Assembled Graphene/Polymer Composite Nanofibers. *ACS Applied Materials & Interfaces*. 6, 17003–17008 (2014). <https://doi.org/10.1021/am504616c>
154. Ly, T.N., Park, S.: Highly sensitive ammonia sensor for diagnostic purpose using reduced graphene oxide and conductive polymer. *Scientific Reports*. 8, 18030 (2018). <https://doi.org/10.1038/s41598-018-36468-z>
155. Zhang, Q., An, C., Fan, S., Shi, S., Zhang, R., Zhang, J., Li, Q., Zhang, D., Hu, X., Liu, J.: Flexible gas sensor based on graphene/ethyl cellulose nanocomposite with ultra-low strain response for volatile organic compounds rapid detection. *Nanotechnology*. 29, 285501 (2018). <https://doi.org/10.1088/1361-6528/aabf2f>
156. Bhati, V.S., Hojamberdiev, M., Kumar, M.: Enhanced sensing performance of ZnO nanostructures-based gas sensors: A review. *Energy Reports*. 6, 46–62 (2020). <https://doi.org/https://doi.org/10.1016/j.egy.2019.08.070>
157. Peng, F., Sun, Y., Yu, W., Lu, Y., Hao, J., Cong, R., Ge, M., Shi, J., Dai, N.: Studies on Sensing Properties and Mechanism of CuO Nanoparticles to H₂S Gas. *Nanomaterials (Basel, Switzerland)*. 10, 774 (2020). <https://doi.org/10.3390/nano10040774>
158. Sten'kin, Y.A., Bolotov, V. V, Sokolov, D. V, Roslikov, V.E., Ivlev, K.E.: Synthesis and Gas-Sensing Properties of MnO₂ – x and MnO₂ – x/CuO-Coated Multiwalled Carbon Nanotube Nanocomposites. *Physics of the Solid State*. 61, 2224–2227 (2019). <https://doi.org/10.1134/S1063783419110386>
159. Mohamed, M.M., Salama, T.M., Morsy, M., Shahba, R.M.A., Mohamed, S.H.: Facile strategy of synthesizing A-MoO_{3-x} nanorods boosted as traced by 1% graphene oxide: Efficient visible light photocatalysis and gas sensing applications. *Sensors and Actuators, B: Chemical*. 299, (2019). <https://doi.org/10.1016/j.snb.2019.126960>
160. Zhang, Z., Zou, R., Song, G., Yu, L., Chen, Z., Hu, J.: Highly aligned SnO₂ nanorods on graphene sheets for gas sensors. *Journal of Materials Chemistry*. 21, 17360–17365 (2011). <https://doi.org/10.1039/C1JM12987B>
161. Majhi, S.M., Mirzaei, A., Kim, H.W., Kim, S.S.: Reduced Graphene Oxide (rGO)-Loaded Metal-Oxide Nanofiber Gas Sensors: An Overview, (2021)
162. Zhang, D., Chang, H., Li, P., Liu, R.: Characterization of nickel oxide decorated-reduced graphene oxide nanocomposite and its sensing properties toward methane gas detection. *Journal of Materials Science: Materials in Electronics*. 27, 3723–3730 (2016). <https://doi.org/10.1007/s10854-015-4214-6>
163. Guo, W., Zhao, B., Zhou, Q., He, Y., Wang, Z., Radacsi, N.: Fe-Doped ZnO/Reduced Graphene Oxide Nanocomposite with Synergic Enhanced Gas Sensing Performance for the Effective Detection of Formaldehyde. *ACS Omega*. 4, 10252–10262 (2019). <https://doi.org/10.1021/acsomega.9b00734>
164. Liu, J., Li, S., Zhang, B., Xiao, Y., Gao, Y., Yang, Q., Wang, Y., Lu, G.: Sensors and Actuators B: Chemical Ultrasensitive and low detection limit of nitrogen dioxide gas sensor based on flower-like ZnO hierarchical nanostructure modified by reduced graphene oxide. *Sensors & Actuators: B. Chemical*. 249, 715–724 (2017). <https://doi.org/10.1016/j.snb.2017.04.190>
165. Li, X., Zhao, Y., Wang, X., Wang, J., Gaskov, A.M., Akbar, S.A.: Reduced graphene oxide (rGO) decorated TiO₂ microspheres for selective room-temperature gas sensors. *Sensors and Actuators B: Chemical*. 230, 330–336 (2016). <https://doi.org/https://doi.org/10.1016/j.snb.2016.02.069>
166. Bandi, S., Hastak, V., Peshwe, D.R., Srivastav, A.K.: In-situ TiO_2 -rGO nanocomposites for CO gas sensing. *Bulletin of Materials Science*. 41, 115 (2018). <https://doi.org/10.1007/s12034-018-1632-0>
167. Galstyan, V., Comini, E., Kholmanov, I., Faglia, G., Sberveglieri, G.: Reduced graphene oxide/ZnO nanocomposite for application in

chemical gas sensors. *RSC Advances*. 6, 34225–34232 (2016). <https://doi.org/10.1039/C6RA01913G>

168. Su, P.-G., Peng, S.-L.: Fabrication and NO₂ gas-sensing properties of reduced graphene oxide/WO₃ nanocomposite films. *Talanta*. 132, 398–405 (2015). <https://doi.org/https://doi.org/10.1016/j.talanta.2014.09.034>

169. Zhang, D., Jiang, C., Liu, J., Cao, Y.: Carbon monoxide gas sensing at room temperature using copper oxide-decorated graphene hybrid nanocomposite prepared by layer-by-layer self-assembly. *Sensors and Actuators B: Chemical*. 247, 875–882 (2017). <https://doi.org/https://doi.org/10.1016/j.snb.2017.03.108>

170. Lin, Q., Li, Y., Yang, M.: Tin oxide/graphene composite fabricated via a hydrothermal method for gas sensors working at room temperature. *Sensors and Actuators B: Chemical*. 173, 139–147 (2012). <https://doi.org/https://doi.org/10.1016/j.snb.2012.06.055>

171. Punetha, D., Pandey, S.K.: Ultrafast and highly selective CO gas sensor based on rGO/Fe₃O₄ nanocomposite at room temperature. In: 2019 IEEE SENSORS. pp. 1–4 (2019)

172. Khaleed, A.A., Bello, A., Dangbegnon, J.K., Madito, M.J., Ugbo, F.U., Akande, A.A., Dhonge, B.P., Barzegar, F., Momodu, D.Y., Mwakikunga, B.W., Manyala, N.: Gas sensing study of hydrothermal reflux synthesized NiO/graphene foam electrode for CO sensing. *Journal of Materials Science*. 52, 2035–2044 (2017). <https://doi.org/10.1007/s10853-016-0491-6>

173. Duraia, E.-S.M., Fahami, A., Beall, G.W.: Microwave-Assisted Synthesis of N-Doped Graphene-Wrapped MnO₂ Nanoflowers. *Journal of Electronic Materials*. 47, 7288–7295 (2018). <https://doi.org/10.1007/s11664-018-6666-y>

174. Chu, J., Wang, X., Wang, D., Yang, A., Lv, P., Wu, Y., Rong, M., Gao, L.: Highly selective detection of sulfur hexafluoride decomposition components H₂S and SOF₂ employing sensors based on tin oxide modified reduced graphene oxide. *Carbon*. 135, 95–103 (2018). <https://doi.org/https://doi.org/10.1016/j.carbon.2018.04.037>

175. Wei, Q., Sun, J., Song, P., Yang, Z., Wang, Q.: Synthesis of reduced graphene oxide/SnO₂ nanosheets/Au nanoparticles ternary composites with enhanced formaldehyde sensing performance. *Physica E: Low-dimensional Systems and Nanostructures*. 118, 113953 (2020). <https://doi.org/https://doi.org/10.1016/j.physe.2020.113953>

176. Basu, S., Hazra, S.: Graphene–Noble Metal Nano-Composites and Applications for Hydrogen Sensors. *C*. 3, 29 (2017). <https://doi.org/10.3390/c3040029>

177. Singhal, A. V., Charaya, H., Lahiri, I.: Noble Metal Decorated Graphene-Based Gas Sensors and Their Fabrication: A Review. *Critical Reviews in Solid State and Materials Sciences*. 42, 499–526 (2017). <https://doi.org/10.1080/10408436.2016.1244656>

178. Zhang, S., Shao, Y., Liao, H., Liu, J., Aksay, I.A., Yin, G., Lin, Y.: Graphene Decorated with PtAu Alloy Nanoparticles: Facile Synthesis and Promising Application for Formic Acid Oxidation. *Chemistry of Materials*. 23, 1079–1081 (2011). <https://doi.org/10.1021/cm101568z>

179. Peng, Y., Ye, J., Zheng, L., Zou, K.: The hydrogen sensing properties of Pt–Pd/reduced graphene oxide based sensor under different operating conditions. *RSC Advances*. 6, 24880–24888 (2016). <https://doi.org/10.1039/C5RA26618A>

180. Choi, M.S., Mirzaei, A., Bang, J.H., Oum, W., Kim, S.S., Kim, H.W.: Improvement of NO₂ Sensing Properties in Pd Functionalized Reduced Graphene Oxides by Electron-Beam Irradiation (2019)

181. Hashtroudi, H., Kumar, R., Savu, R., Moshkalev, S., Kawamura, G., Matsuda, A., Shafiei, M.: Hydrogen gas sensing properties of microwave-assisted 2D Hybrid Pd/rGO: Effect of temperature, humidity and UV illumination. *International Journal of Hydrogen Energy*. 46, 7653–7665 (2021). <https://doi.org/https://doi.org/10.1016/j.ijhydene.2020.11.268>

182. Karaduman, I., Er, E., Çelikkan, H., Erk, N., Acar, S.: Room-temperature ammonia gas sensor based on reduced graphene oxide nanocomposites decorated by Ag, Au and Pt nanoparticles. *Journal of Alloys and Compounds*. 722, 569–578 (2017). <https://doi.org/https://doi.org/10.1016/j.jallcom.2017.06.152>

183. Fan, Y.-Y., Tu, H.-L., Pang, Y., Wei, F., Zhao, H.-B., Yang, Y., Ren, T.-L.: Au-decorated porous structure graphene with enhanced sensing performance for low-concentration NO₂ detection. *Rare Metals*. 39, 651–658 (2020). <https://doi.org/10.1007/s12598-020-01397-2>

184. Luo, Y., Zhang, D., Fan, X.: Hydrothermal Fabrication of Ag-Decorated MoSe₂/Reduced Graphene Oxide Ternary Hybrid for H₂S Gas Sensing. *IEEE Sensors Journal*. 20, 13262–13268 (2020). <https://doi.org/10.1109/JSEN.2020.3006983>

185. Ouda, E., Elzwawy, A., Duraia, E.-S.M.: A facile microwave irradiation synthesis of GO/CNTs hybrids doped with MnO₂: structural and magnetic

analysis. *Applied Physics A*. 127, 676 (2021). <https://doi.org/10.1007/s00339-021-04842-w>

186. Jeong, H.Y., Lee, D.-S., Choi, H.K., Lee, D.H., Kim, J.-E., Lee, J.Y., Lee, W.J., Kim, S.O., Choi, S.-Y.: Flexible room-temperature NO₂ gas sensors based on carbon nanotubes/reduced graphene hybrid films. *Applied Physics Letters*. 96, 213105 (2010). <https://doi.org/10.1063/1.3432446>

187. Morsy, M., Yahia, I.S., Zahran, H.Y., Meng, F., Ibrahim, M.: Portable and Battery Operated Ammonia Gas Sensor Based on CNTs / rGO / ZnO Nanocomposite. 48, 7328–7335 (2019). <https://doi.org/10.1007/s11664-019-07550-7>

188. Srivastava, V., Jain, K.: At room temperature graphene/SnO₂ is better than MWCNT/SnO₂ as NO₂ gas sensor. *Materials Letters*. 169, 28–32 (2016). <https://doi.org/https://doi.org/10.1016/j.matlet.2015.12.115>

189. Idowu, A., Boesl, B., Agarwal, A.: 3D graphene foam-reinforced polymer composites – A review. *Carbon*. 135, 52–71 (2018). <https://doi.org/10.1016/j.carbon.2018.04.024>

190. Hu, G., Xu, C., Sun, Z., Wang, S., Cheng, H.-M., Li, F., Ren, W.: 3D Graphene-Foam-Reduced-Graphene-Oxide Hybrid Nested Hierarchical Networks for High-Performance Li-S Batteries. *Advanced Materials*. 28, 1603–1609 (2016). <https://doi.org/https://doi.org/10.1002/adma.201504765>

191. Ussia, M., Bruno, E., Spina, E., Vitalini, D., Pellegrino, G., Ruffino, F., Privitera, V., Carroccio, S.C.: Freestanding photocatalytic materials based on 3D graphene and polyporphyrins. *Scientific Reports*. 8, 5001 (2018). <https://doi.org/10.1038/s41598-018-23345-y>

192. Wang, H., Mi, X., Li, Y., Zhan, S.: 3D Graphene-Based Macrostructures for Water Treatment. *Advanced Materials*. 32, 1806843 (2020). <https://doi.org/https://doi.org/10.1002/adma.201806843>

193. Venkateshalu, S., Grace, A.N.: Review—Heterogeneous 3D Graphene Derivatives for Supercapacitors. *Journal of The Electrochemical Society*. 167, 050509 (2020). <https://doi.org/10.1149/1945-7111/ab6bc5>

194. He, S., Chen, W.: 3D graphene nanomaterials for binder-free supercapacitors: scientific design for enhanced performance. *Nanoscale*. 7, 6957–6990 (2015). <https://doi.org/10.1039/C4NR05895J>

195. Thomas, T., Agarwal, A.: A Facile and Scalable Approach in the Fabrication of Tailored 3D Graphene Foam via Freeze Drying, (2021)

196. Liu, Q., Zhong, H., Chen, M., Zhao, C., Liu, Y., Xi, F., Luo, T.: Functional nanostructure-loaded three-dimensional graphene foam as a non-enzymatic electrochemical sensor for reagentless glucose detection. *RSC Advances*. 10, 33739–33746 (2020). <https://doi.org/10.1039/D0RA05553K>

197. Yavari, F., Chen, Z., Thomas, A. V., Ren, W., Cheng, H.M., Koratkar, N.: High sensitivity gas detection using a macroscopic three-dimensional graphene foam network. *Scientific Reports*. 1, 1–5 (2011). <https://doi.org/10.1038/srep00166>

198. Ha, N.H., Thinh, D.D., Huong, N.T., Phuong, N.H., Thach, P.D., Hong, H.S.: Fast response of carbon monoxide gas sensors using a highly porous network of ZnO nanoparticles decorated on 3D reduced graphene oxide. *Applied Surface Science*. 434, 1048–1054 (2018). <https://doi.org/https://doi.org/10.1016/j.apsusc.2017.11.047>

199. Morsy, M., Madbouly, A.I.: Sensors and Actuators A: Physical Room temperature xylene sensor based on Co₃O₄ / GF hybrid. *Sensors & Actuators: A. Physical*. 305, 111921 (2020). <https://doi.org/10.1016/j.sna.2020.111921>

الملخص العربي

المواد الكربونية النانومترية ومتراباتها وتطبيقاتها كحساسات للغاز : مقالة مرجعية

اثارت النتائج المترتبة على دمج المواد الكربونية في المدى النانومتري لتطبيقات حساسات الغاز الاهتمام في السنوات القريبه المنقضية. طبقا للخواص الفيزيائية والكيميائية المرغوبه للمركبات الكربونية النانومترية ومتراباتها المختلفه فانها تتناسب مع تطبيقات حساسات الغاز حيث انها تستوفى شرط مساحة السطح الكبيره وكذلك فجوة الطاقه المنخفضه. في هذه مقاله المرجعيه نبدأ باستعراض اهمية وطرق تحضير المواد الكربونية للتركيبات المتنوعه مثل (carbon nanooxions), (carbon naohorns), الجرافين (nanodiamonds), and (carbon quantum dots) ومشتقاته المتنوعه يتم دمجها عامه مع انابيب الكربون النانومترية. في الجزء التالي لما سبق نطرق الى طرق تحضير الجرافين وخصائصه ومترابكات الجرافين-الاكاسيد المعدنيه و الجرافين - العناصر النيبيله و الجرافين-المواد البوليمريه المطبقه لحساسات الغاز. هذه مقاله المرجعيه تلخص النقاط الاساسيه والمؤثره لتطبيقات حساسات الغاز المعتمده على المواد الكربونية في المدى النانومتري. اضافة لما سبق فانه تم مناقشة واستعراض حساسات الغاز لانواع مختلفه من الغازات.